

---

## NITRONIC 60 Stainless Steel

---

**NOW AVAILABLE IN BAR, WIRE, SHEET,  
PLATE, WELD WIRE, HIGH STRENGTH  
SHAFTING, AND MADE TO ORDER ITEMS.**

- **FIGHTS GALLING AND WEAR**
- **STRONGER THAN 304 / 316 SS**

---

## Applications Potential

Outstanding galling resistance at both ambient and elevated temperatures makes patented NITRONIC® 60 Stainless Steel a valuable material for valve stems, seats and trim; fastening systems, including nuts and bolts; screening; chain-drive systems; pins, bushings and roller bearings; and pump components such as wear rings and lobes. NITRONIC 60 is the most effective wear and galling resistant alloy for bridge pins and other critical construction applications.

---



**NITRONIC 60  
STAINLESS STEEL  
BAR AND WIRE  
(UNS-S21800)**

# Contents

Applications Potential .....	2
Composition.....	2
Available Forms .....	2
Specifications.....	2
Heat Treatment.....	2
Metric Practice .....	3
Galling Resistance .....	3
Wear Resistance .....	6
Effect of Hardness .....	10
Austenitic Stainless Steels	
Effect of Surface Finish.....	10
Effect of Hardness .....	11
Heat Treatable Steels	
Effect of Load.....	12
Effect of Speed .....	13
Effect of Distance.....	14
Elevated Temperature	
Wear .....	16
Cavitation Erosion.....	17
Abrasion Resistance .....	18
Corrosion Resistance .....	18
Oxidation Resistance.....	21
Elevated Temperature.....	22
Corrosion Resistance	
Mechanical Properties .....	22
Room Temperature	
Mechanical Properties .....	25
Elevated Temperature	
Mechanical Properties .....	26
Cryogenic Temperature	
High Strength Bar	
Properties.....	27
Physical Properties .....	28
Machinability .....	29
Welding .....	30
Forging.....	31
Casting.....	31

The information and data in this product data bulletin are accurate to the best of our knowledge and belief, but are intended for general information only. Applications suggested for the materials are described only to help readers make their own evaluations and decisions, and are neither guarantees nor to be construed as expressed or implied warranties of suitability for these or other applications.

Data referring to mechanical properties and chemical analyses are the result of tests performed on specimens obtained from specific locations of the products in accordance with prescribed sampling procedures; any warranty thereof is limited to the values obtained at such locations and by such procedures. There is no warranty with respect to values of the materials at other locations.

Waspaloy is a trademark of Pratt & Whitney Aircraft Div., United Technologies Corp.

Waukesha is a trademark of Waukesha Foundry Co.

Colmonoy is a trademark of Wall Colmonoy.

Astralloy is a trademark of Astralloy Vulcan Corp.

Armco, the Armco Triangle, NITRONIC, 17-4 PH, 15-5 PH, 17-7 PH, and PH 13-8 Mo are registered trademarks of AK Steel.

Hastelloy and Haynes are trademarks of Haynes International. Stellite and Tribaloy are trademarks of Deloro Stellite. Inc. Inconel and Monel are trademarks of International Nickel Co. Inc.

## NITRONIC 60 Stainless Steel Product Description

NITRONIC 60 Stainless Steel provides a significantly lower cost way to fight wear and galling compared with cobalt-bearing and high nickel alloys. Its uniform corrosion resistance is better than Type 304 in most media. Chloride pitting resistance is superior to Type 316. Room temperature yield strength is nearly twice that of Types 304 and 316. In addition, NITRONIC 60 Stainless Steel provides excellent high-temperature oxidation resistance and low-temperature impact resistance.

## Composition

	% Min	% Max
Carbon	0.060	0.080
Manganese	7.50	8.50
Phosphorus		0.040
Sulfur		0.030
Silicon	3.70	4.20
Chromium	16.00	17.00
Nickel	8.00	8.50
Molybdenum		0.75
Copper		0.75
Nitrogen	0.10	0.18
Titanium		0.050
Aluminum		0.020
Boron		0.0015
Columbium		0.10
Tin		0.050
Vanadium		0.20
Tungsten		0.15

## Available Forms

NITRONIC 60 Stainless Steel is available in bar, master alloy pigs, ingots and forging billets. Forms available from other manufacturers using melt include sheet and strip, castings, extrusions, seamless tubing and plate. NITRONIC 60 Stainless Steel is covered by U.S. Patent 3,912,503.

## Specifications

NITRONIC 60 Stainless Steel is listed as Grade UNS S21800 in: ASTM A276-Bars and Shapes  
ASTM A314-Stainless and Heat-Resisting Steel Billets and Bars for Forging  
ASTM A479-Bars and Shapes for Use in Boilers and Other Pressure Vessels  
ASTM A580-Wire  
ASTM A 193-Bolting (Grade B8S)  
ASTM A 194-Nuts (Grade 8S)  
ASTM A240-Heat-Resisting Chromium and Chromium-Nickel Stainless Steel Plate, Sheet and Strip for Pressure Vessels  
ASTM A351-Austenitic Steel Castings for High Temperature Service (Grade CF IOS MnN)  
ASTM A 743-Corrosion Resistant Iron-Chromium, Iron-Chromium-Nickel and Nickel-Base Alloy Castings for General Application (Grade CF 10SMnN)  
AMS 5848-Bars, Forgings, Extrusions, Tubing and Rings  
ASME Design Allowables Listed in Table UHA-23 of Section VIII, Division 1 ASME Design Values Listed in Section III, Division 1, Table 1-72

## Metric Practice

The values shown in this bulletin were established in U.S. customary units. The metric equivalents of U.S. customary units shown may be approximate. Conversion to the metric system, known as the International System of Units (SI), has been accomplished in accordance with the American Iron and Steel Institute Metric Practice Guide, 1978.

The Newton (N) has been adopted by the IS as the metric standard unit of force as discussed in the AISI Metric Practice Guide. The term for force per unit of area (stress) is the newton per square meter (N/m<sup>2</sup>). Since this can be a large number, the prefix mega is used to indicate 1,000,000 units and the term meganewton per square meter (MN/m<sup>2</sup>) is used. The unit (N/m<sup>2</sup>) has been designated a Pascal (Pa).

The relationship between the U.S. and the SI units for stress is: 1000 pounds/in<sup>2</sup> (psi) = 1 kip/in<sup>2</sup> (ksi) = 6.8948 meganewtons/m<sup>2</sup> (MN/m<sup>2</sup>) = 6.8948 megapascals (MPa). Other units are discussed in the Metric Practice Guide.

## Galling Resistance

Galling is the tearing of metal surfaces which suddenly renders a component unserviceable. Galling is a major concern in two application areas in particular - threaded assemblies and valve trim. Armco uses a button and block galling test to rank alloys for their galling tendencies. In the test procedure, a dead-load weight is applied in a Rockwell C Hardness Tester on two flat, polished surfaces (10-20 microinches). The 0.5-inch (12.7 mm) diameter button


is slowly rotated by hand 360 under the load and then examined for galling at a 7X magnification. If galling has not occurred, new specimens are tested at higher stresses until galling is observed. The threshold galling stress is selected as the stress midway between the highest nongalled stress and the stress where galling was first observed. Results are reproducible within  $\pm 2.5$  ksi (18 MPa). However, this test should not be used for design purposes because of the many unknown variables in a particular application. The test has proven highly successful as a method of screening alloys for prototype service evaluation. For further details of the test procedure, see April, 1973, Materials Engineering, page 60.

Table 1  
**Unlubricated Galling Resistance of Stainless Steels**  
**Threshold Galling Stress in ksi (MPa)**  
**(Stress at which galling began)**

Conditions & Nominal Hardness (Brinell)	Type 410	Type 416	Type 430	Type 440C	Type 303	Type 304	Type 316	17-4 PH	NITRONIC 32	NITRONIC 60
Hardened & Stress Relieved (352) Type 410	3 (21)	4 (28)	3 (21)	3 (21)	4 (28)	2 (14)	2 (14)	3 (21)	46 (317)	50 + (345)
Hardened & Stress Relieved (342) Type 416	4 (28)	13 (90)	3 (21)	21 (145)	9 (62)	24 (165)	42 (290)	2 (14)	45 (310)	50 + (345)
Annealed (159) Type 430	3 (21)	3 (21)	2 (14)	2 (14)	2 (14)	2 (14)	2 (14)	3 (21)	8 (55)	36 (248)
Hardened & Stress Relieved (560) Type 440C	3 (21)	21 (145)	2 (14)	11 (76)	5 (34)	3 (21)	37 (255)	3 (21)	50 + (345)	50 + (345)
Annealed (153) Type 303	4 (28)	9 (62)	2 (14)	5 (34)	2 (14)	2 (14)	3 (21)	3 (21)	50 + (345)	50 + (345)
Annealed (140) Type 304	2 (14)	24 (165)	2 (14)	3 (21)	2 (14)	2 (14)	2 (14)	2 (14)	30 (207)	50 + (345)
Annealed (150) Type 316	2 (14)	42 (290)	2 (14)	37 (255)	3 (21)	2 (14)	2 (14)	2 (14)	3 (21)	38 (262)
H 950 (415) 17-4 PH	3 (21)	2 (14)	3 (21)	3 (21)	2 (14)	2 (14)	2 (14)	2 (14)	50 + (345)	50 + (345)
Annealed (235) NITRONIC 32	46 (317)	45 (310)	8 (55)	50 + (345)	50 + (345)	30 (207)	3 (21)	50 + (345)	30 (207)	50 + (345)
Annealed (205) NITRONIC 60	50 + (345)	50 + (345)	36 (248)	50 + (345)	50 + (345)	50 + (345)	38 (262)	50 + (345)	50 + (345)	50 (345)

+ Did Not Gall

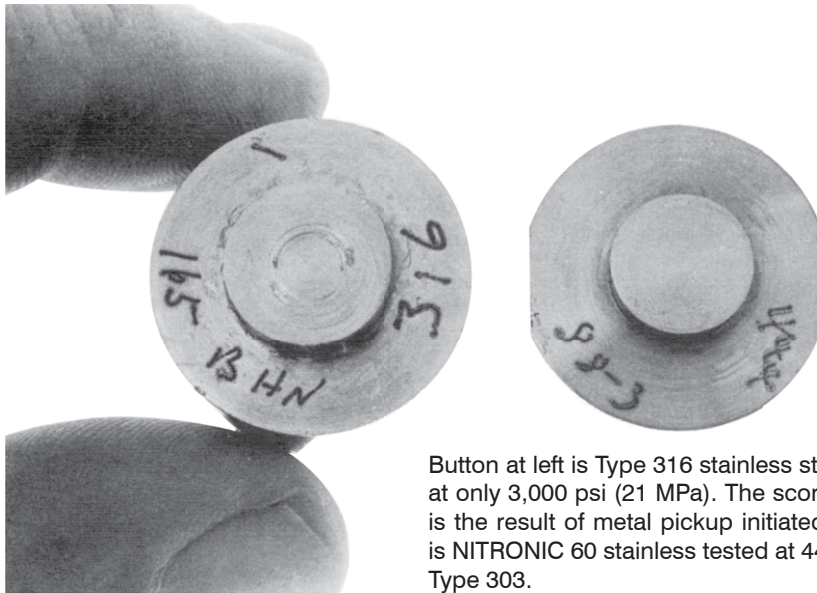(Note condition and hardness apply to both horizontal and vertical axes.)



Button at left is Type 316 stainless steel tested against Type 304 at only 3,000 psi (21 MPa). The scoring shown on the Type 316 is the result of metal pickup initiated by galling. Button at right is NITRONIC 60 stainless tested at 44,000 psi (303 MPa) against Type 303.

Table 2

**Unlubricated Galling Resistance of Several Metal Combinations**

Couple - (Brinell Hardness)	Threshold Galling Stress ksi (MPa) (Stress at which galling began)
Waukesha 88 (141) vs. Type 303 (180)	50 + (345)
Waukesha 88 (141) vs. Type 201 (202)	50 + (345)
Waukesha 88 (141) vs. Type 316 (200)	50 + (345)
Waukesha 88 (141) vs. 17-4 PH (405)	50 + (345)
Waukesha 88 (141) vs. 20 Cr-80 Ni (180)	50 + (345)
Waukesha 88 (141) vs. Type 304 (207)	50 + (345)
Silicon Bronze (200) vs. Silicon Bronze (200)	4 (28)
A-286 (270) vs. A-286 (270)	3 (21)
NITRONIC 60 (205) vs. A-286 (270)	49 + (338)
NITRONIC 60 (205) vs. 20 Cr-80 Ni (180)	36 (248)
NITRONIC 60 (205) vs. Ti-6Al-4V (332)	50 + (345)
AISI 4337 (484) vs. AISI 4337 (415)	2 (14)
AISI 1034 (415) vs. AISI 1034 (415)	2 (14)
NITRONIC 60 (205) vs. AISI 4337 (448)	50 + (345)
NITRONIC 60 (205) vs. Stellite 6B (415)	50 + (345)
NITRONIC 32 (234) vs. AISI 1034 (205)	2 (14)
NITRONIC 32 (231) vs. Type 201 (202)	50 + (345)
NITRONIC 60 (205) vs. 17-4 PH (322)	50 + (345)
NITRONIC 60 (205) vs. NITRONIC 50 (205)	50 + (345)
NITRONIC 60 (205) vs. PH 13-8 Mo (297)	50 + (345)
NITRONIC 60 (205) vs. PH 13-8 Mo (437)	50 + (345)
NITRONIC 60 (205) vs. 15-5 PH (393)	50 + (345)
NITRONIC 60 (205) vs. 15-5 PH (283)	50 + (345)
NITRONIC 60 (205) vs. 17-7 PH(404)	50 + (345)
NITRONIC 60 (205) vs. NITRONIC 40 (185)	50 + (345)
NITRONIC 60 (205) vs. Type 410 (240)	36 (248)
NITRONIC 60 (205) vs. Type 420 (472)	50 + (345)
NITRONIC 60 (210) vs. Type 201 (202)	46 + (317)
NITRONIC 60 (210) vs. AISI 4130 (234)	34 (234)
NITRONIC 60 (205) vs. Type 301 (169)	50 + (345)
Type 440C (600) vs. Type 420 (472)	3 (21)
Type 201 (202) vs. Type 201 (202)	20 (137)

Table 2 Continued

Couple - (Brinell Hardness)	Threshold Galling Stress ksi (MPa) (Stress at which galling began)
NITRONIC 60 (205) vs. Cr plated Type 304	50 + (345)
NITRONIC 60 (205) vs. Cr plated 15-5PH (H 1150)	50 + (345)
NITRONIC 60 (205) vs. Inconel 718 (306)	50 + (345)
NITRONIC 60 (205) vs. CP Titanium (185)	47 + (324)
NITRONIC 60 (205) vs. Ni Resist Type 2 (145)	50 + (345)
NITRONIC 60 (205) vs. Stellite 21 (295)	43 + (296)
Type 201 (202) vs. Type 304 (140)	2 (14)
Type 201 (202) vs. 17-4 PH (382)	2 (14)
Type 410 (322) vs. Type 420 (472)	3 (21)
Type 304 (140) vs. AISI 1034 (205)	2 (14)
Type 304 (337) vs. Type 304 (337)	2 (14)
Type 304 (207) vs. Type 304 (337)	2 (14)
Duplex 2205 (235) vs. Type 303 (153)	2 (14)
Duplex 2205 (235) vs. Type 304 (270)	2 (14)
Duplex 2205 (235) vs. Type 316 (150)	2 (14)
Duplex 2205 (235) vs. Type 416 (342)	2 (14)
Duplex 2205 (235) vs. 17-4 PH (415)	2 (14)
Duplex 2205 (235) vs. NITRONIC 60 (210)	30 (207)
IN 625 (215) vs. Type 303 (153)	2 (14)
IN 625 (215) vs. Type 304 (270)	2 (14)
IN 625 (215) vs. Type 316 (161)	2 (14)
IN 625 (215) vs. 17-4 PH (415)	2 (14)
IN 625 (215) vs. NITRONIC 60 (210)	33 (227)
Stellite 21 (270) vs. Type 316 (161)	2 (14)
Stellite 21 (270) vs. NITRONIC 50 (210)	2 (14)
Stellite 21 (270) vs. NITRONIC 60 (210)	43 + (297)
K-500 Monel (321) vs. Type 304 (270)	2 (14)
K-500 Monel (321) vs. Type 316 (161)	2 (14)
K-500 Monel (321) vs. 17-4 PH(415)	2 (14)
K-500 Monel (321) vs. NITRONIC 50 (245)	2 (14)
K-500 Monel (321) vs. NITRONIC 60 (210)	17 (117)
NITRONIC 60 (210) vs. Tribaloy 700 (437)	45 + (310)
Stellite 68 (450) vs. Type 316 (61)	8 (55)
Stellite 68 (450) vs. Type 304 (150)	47 + (324)
Stellite 68 (450) vs. NITRONIC 60 (210)	50+ (345)
Type 410 (210) vs. Type 410 (210)	2 (14)
Type 410 (363) vs. Type 410 (363)	2 (14)
Type 410 (210) vs. Type 410 (363)	2 (14)
17-4 PH (H 1150 + H 1150) (313)	2 (14)
Type 410 (210) vs. 17-4 PH (H 1150 + H 1150) (313)	2 (14)
NITRONIC 60 (210) vs. 17-4 PH (H 1150 + H 1150) (313)	21 (145)
NITRONIC 60 (210) vs. Type 410 (210)	24 (165)

+ Did not gall

Table 3  
Cryogenic Galling Resistance\*

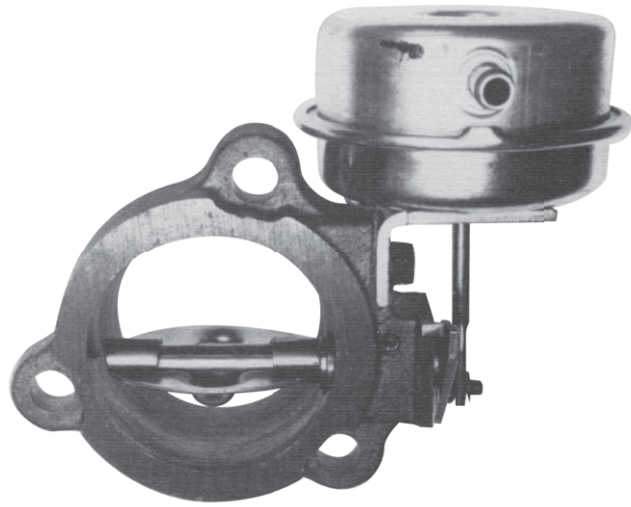
Couple-(Brinell Hardness)	Threshold Galling Stress ksi (MPa) Stress at which galling began)
NITRONIC 60 (189) vs. NITRONIC 60 (189)	50 + (345)
NITRONIC 60 (189) vs. Type 410 (400)	50 + (345)
NITRONIC 60 (189) vs. 17-4 PH (415)	50 + (345)
NITRONIC 60 (189) vs. Type 304 (178)	50 + (345)
17-4 PH (404) vs. Type 410 (400)	7 (48)
Type 304 (178) vs. Type 410 (400)	22 (152)

+Did not gall.

• Tested in liquid nitrogen -320F ( -196 C).


## Elevated Temperature Galling Applications

NITRONIC 60 Stainless Steel has performed successfully in elevated temperature service for valve trim. Several austenitic stainless steels were evaluated as stems and bushings in an automotive emissions control butterfly valve. However, only NITRONIC 60 operated smoothly over the entire temperature range. The other alloys galled in the 800-1500°F (427-816°C) temperature range. Another application involved a 20-inch (508 mm) gate valve which opened and closed every 170 seconds at 750°F (399°C). NITRONIC 60 weld overlay on the seat and disk lasted 140 days without galling which would have quickly contaminated the process. A similar valve with Stellite 6B hard faced trim lasted only 90 days.



## Wear Resistance

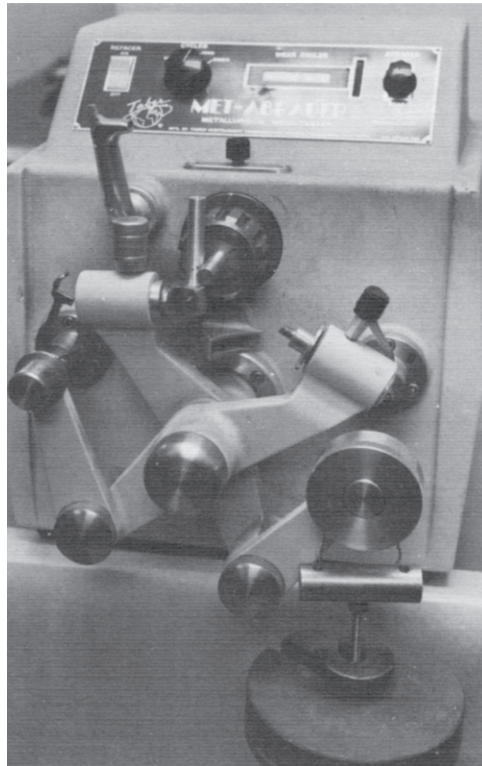Data shown in Tables 4 through 16 and Figure 1, were developed under the following test conditions: Taber Met-Abrader machine, 0.500-inch (12.7 mm) crossed 90° cylinders, no lubricant, 16-pound (71 N) load, 105 RPM (and 415 RPM where noted), room temperature, 120 grit surface finish, 10,000 cycles, degreased in acetone, duplicate tests, weight loss corrected for density differences.



Taber Met-Abrader crossed cylinder wear test.

Table 4

**Wear Compatibility of Self-Mated Austenitic Stainless Steels**

Alloy	Hardness Rockwell	Weight Loss. mg/1,000 cycles	
		@105 RPM	@415 RPM
NITRONIC 60	B95	2.79	1.58
Type 201	B90	4.95	4.68
Type 301	B90	5.47	5.70
Type 302B	B90	5.47	4.62
NITRONIC 32	B95	7.39	3.08
NITRONIC 33	B94	7.95	4.35
NITRONIC 40	B93	8.94	5.35
NITRONIC 50	B99	9.95	4.60
Type 310	B72	10.40	6.49
Type 316	B91	12.50	7.32
Type 304	B99	12.77	7.59
Duplex 2205	B99	17.40	4.02
21-4N	C33	21.38	10.02
Type 303	B99	386.10	50.47

Table 5

**Wear Compatibility of Self-Mated Martensitic and Ferritic Stainless Steels**

Alloy	Hardness Rockwell	Weight Loss. mg/1,000 cycles	
		@105 RPM	@415 RPM
Type 440C	C57	3.81	0.54
PH 13-8 Mo	C47	38.11	5.41
17-4 PH	C43	52.80	12.13
Type 416	C39	58.14	99.78
PH 13-8 Mo	C32.5	60.15	10.95
Type 430 (5000 cycles)	B94	120.00	69.93
Type 440C	C35	153.01	163.35
Type 420 (5000 cycles)	C46	169.74	12.73
Type 431 (5000 cycles)	C42	181.48	10.35
Type 410	C40	192.79	22.50

Table 6

**Wear Compatibility of Self-Mated Cast Alloys and Coatings**

Alloy or Coating	Hardness Rockwell	Weight Loss. mg/1,000 cycles	
		@105 RPM	@415 RPM
Ni-Hard	C44.5	0.13	0.39
Tuffrided PH	C70	0.33	-
White Cast Iron	C60	0.38	0.20
Tribaloy 800	C54.5	0.65	0.37
Tribaloy 700	C45	0.93	0.50
Borided AISI 1040	C70	1.01	2.08
Colmonoy 6	C56	1.06	0.58
Stellite 31	C24	1.65	6.04
Chrome Plate	--	1.66	1.28
Nitrided PH	--	-	1.11
Ni-Resist Type 1	B80	4.45	508.52
Ni-Resist Type 2	B80	8.80	522.32
Waukesha 88	B81	7.09	6.10
Inconel	C25	19.67	2.67
HN	B78	21.75	2.94
CA6-NM	C26	130.41	55.60

Table 7

**Wear Compatibility of Self-Mated Various Wrought Alloys**

Alloy	Hardness Rockwell	Weight Loss. mg/1,000 cycles	
		@105 RPM	@415 RPM
D2 Tool Steel	C61	0.46	0.34
AISI 4337	C52	0.73	0.48
Stellite 6B	C48	1.00	1.27
Hadfield Mn Steel	B95	1.25	0.41
Haynes 25	C28	1.75	23.52
Aluminum Bronze (10.5 Al)	B87	2.21	1.52
Be-Cu	C40	2.97	2.56
Silicon Bronze	B93	5.57	4.18
Ti-6Al-4V	C36	7.64	4.49
Inconel 718	C38	9.44	2.85
AISI 4130	C47	9.44	6.80
Waspaloy	C36	11.25	3.28
Inconel 625	B96	11.34	3.49
Hastelloy C	B95.5	13.88	4.50
20 Cb-3	B99	16.47	7.22
6061-T6 Aluminum	B59	17.06	21.15
A-286	C33	17.07	7.62
Inconel X750	C36	18.70	5.56
H 13 Tool Steel	C45	20.74	10.15
K-500 Monel	C34	30.65	23.87
20 Cr-80 Ni	B87	44.91	13.92
Copper	B49	57.01	29.25
Leaded Brass	B72	127.91	67.12
AISI 1034	B95	134.05*	106.33
Nickel	B40	209.72	110.25
Astralloy V	C46	213.58	8.22
AISI 4130	C32	257.59	262.64

\*5,000 cycles

Table 8

**Wear Compatibility of Stainless Steel Couples**

Alloy	Weight Loss. mg/1,000 cycles							
	vs.	Type 304	Type 316	17-4 PH	NITRONIC 32	NITRONIC 50	NITRONIC 60	Type 440C
Hardness Rockwell		B99	B91	C43	B95	B99	B95	C57
Type 304		12.8						
Type 316		10.5	12.5					
17-4 PH		24.7	18.5	52.8				
NITRONIC 32		8.4	9.4	17.2	7.4			
NITRONIC 50		9.0	9.5	15.7	8.3	10.0		
NITRONIC 60		6.0	4.3	5.4	3.2	3.5	2.8	
Type 440C		4.1	3.9	11.7	3.1	4.3	2.4	3.8

Table 9  
**Wear Compatibility of Corrosion-Resistant Couples**

Alloy	Weight Loss. mg/1,000 cycles			
	vs.	Silicon Bronze	Chrome Plate	Stellite 6B
Hardness Rockwell		B93	(-)	C48
Type 304 (B99)		2.1	2.3	3.1
17-4 PH (C43)		2.0	3.3	3.8
NITRONIC 32 (B95)		2.3	2.5	2.0
NITRONIC 60 (B95)		2.2	2.1	1.9
Silicon Bronze		5.6	1.3	1.9
Chrome Plate			1.7	0.33
Stellite 68				1.00

Table 10  
**Wear Compatibility of NITRONIC 60 Compared with 17-4 PH and Stellite 6B Against Various Alloys**

Alloy	Hardness Rockwell	Weight loss of Couple (mg/1000 cycles)		
		17-4 PH (C43)	NITRONIC 60 (B95)	Stellite 6B (C48)
Type 304	B99	24.7	6.0	3.1
Type 316	B91	18.5	4.3	5.5
17-4 PH	C31.5	66.1	4.9	2.7
17-4 PH	C43	52.8	5.4	3.8
NITRONIC 32	B95	17.2	3.2	2.0
NITRONIC 50	B99	15.7	3.5	2.9
NITRONIC 60	B95	5.4	2.8	1.9
Stellite 68	C48	3.8	1.9	1.0
Chrome Plate	—	3.3	2.1	0.3
Silicon Bronze	B93	2.0	2.2	1.9
K-500 Monel	C34	34.1	22.9	18.8
Type 416	C24	—	5.5	43.0
Type 431	C32	—	3.0	1.0
Waspaloy	C36	—	3.1	2.4
Inconel 718	C38	—	3.1	2.7
Inconel X-750	C36	—	5.5	8.0

Table 11  
**Comparative Sliding Compatibility of NITRONIC 60 Stainless Steel and Waukesha 88 in Contact with Stainless Steels**

Alloy	Weight Loss. mg/1,000 cycles	
	vs. NITRONIC 60	Waukesha 88
Hardness Rockwell	B95	B81
NITRONIC 60 (B95)	2.79	8.44
Waukesha 88 (B81)	8.44	7.09
Type 304 (B99)	6.00	8.14
Type 316 (B91)	4.29	9.55
Type 440C (C57)	2.36	6.90
17-4 PH (C43)	5.46	9.12
NITRONIC 32 (B95)	3.18	7.57

Table 12

**Wear of Type 410 and 17-4 PH in NACE-Approved Conditions for Sour Well Service**

Alloy Couple (Rockwell Hardness)	Weight Loss. mg/1,000 cycles	
	@105 RPM	@415 RPM
Type 410 (B95) — Self	261.07	115.69
17-4 PH (C34, Condition H 1150 + H 1150) — Self	75.42	26.80
17-4 PH (C34, Condition H 1150 + H 1150) — Type 410 (B95)	104.80	58.94
17-4 PH (C34, Condition H 1150 + H 1150) — NITRONIC 60 (B95)	4.14	4.34
Type 410 (B95) — NITRONIC 60 (B95)	3.81	5.19

Table 13

**Wear Compatibility of Miscellaneous Dissimilar Couples**

Couple (Rockwell Hardness)	Couple Weight Loss (mg/1000 cycles)
NITRONIC 60 (B95) vs. Type 431 (C32)	3.01
NITRONIC 60 (B95) vs. Type 431 (C42)	3.01
NITRONIC 60 (B95) vs. Type 416 (C39)	16.5
NITRONIC 60 (B95) vs. 17-4 PH (C31.5)	4.91
NITRONIC 60 (B95) vs. Type 301 (B90)	2.74
NITRONIC 60 (B95) vs. Type 303 (B98)	144.3
NITRONIC 60 (B95) vs. K-500 (C34)	22.9
NITRONIC 60 (B95) vs. A-286 (C33)	5.86
NITRONIC 60 (B95) vs. AISI 4337 (C52)	2.50
NITRONIC 60 (B95) vs. 02 Tool Steel (C61)	1.94
NITRONIC 60 (B95) vs. Ni-Hard (C44.5)	2.19
NITRONIC 60 (B95) vs. Tufftrided PH	2.72
NITRONIC 60 (B95) vs. Borided AISI 1040	2.53
NITRONIC 60 (B95) vs. Tribaloy 700 (C45)	2.08
NITRONIC 60 (B95) vs. Tribaloy 800 (C54.5)	1.34
NITRONIC 60 (B95) vs. Haynes 25 (C28)	2.10
NITRONIC 60 (B95) vs. PH 13-8 Mo (C44)	3.74
NITRONIC 60 (B95) vs. AISI 1040 (B95)	4.09
NITRONIC 60 (B95) vs. Inconel 625 (B99)	3.20
17-4 PH (C43) vs. Type 440C (C34)	113.6
17-4 PH (C43) vs. A-286 (C33)	15.5
17 -4 PH (C43) vs. K-500 (C34)	34.1
17 -4 PH (C43) vs. D2 Tool Steel (C61)	5.69
17-4 PH (C43) vs. Ni-Hard (C44.5)	4.58
17 -4 PH (C43) vs. Haynes 25 (C28)	1.46
17 -4 PH (C43) vs. Ti-6Al-4V (C36)	11.7
17 -4 PH (C43) vs. Borided AISI 1040	11.7
17-4 PH (C43) vs. Inconel 625 (899)	8.84
X 750 (C36) vs. A-286 (C33)	16.7
X 750 (C36) vs. Haynes 25 (C28)	2.10
X 750 (C36) vs. Ti-6Al-4V (C36)	7.85
Type 304 (B99) vs. 02 Tool Steel (C61)	3.33
Type 316 (B91) vs. K-500 (C34)	33.8
NITRONIC 32 (B95) vs. Type 416 (C39)	34.8
NITRONIC 32 (B95) vs. Type 431 (C42)	4.86
NITRONIC 50 (B99) vs. Tufftrided PH	7.01
Type 416 (C39) vs. Be-Cu (C40)	4.12
Type 431 (C32) vs. Stellite 68 (C48)	2.08
Type 431 (C42) vs. Stellite 68 (C48)	0.66

Table 14  
**Effect of Hardness on the Wear Resistance  
of Austenitic Stainless Steels**

Self-Mated Series  
Weight Loss of Test Couple (mg/1000 cycles)

Type 316L			NITRONIC 60			NITRONIC 50		
HRB 72	vs. HRB 72	11.58	HRB 92	vs. HRB 92	3.09	HRB 99	vs. HRB 99	9.95
HRB 76	vs. HRB 76	11.86	HRC 29	vs. HRC 29	3.12	HRC 28	vs. HRC 28	9.37
HRC 24	vs. HRC 24	12.54	HRB 92	vs. HRC 29	3.40	HRC 38	vs. HRC 38	9.26
HRC 29	vs. HRC 29	12.51				HRB 99	vs. HRC 38	9.31
HRC 30.5	vs. HRC 30.5	12.52						
HRB 72	vs. HRC 30.5	12.06						
HRB 76	vs. HRC 29	12.34						

Table 15  
**Effect of Hardness on the Wear Resistance  
of Austenitic Stainless Steels**

Dissimilar Couple Series  
Weight Loss of Test Couple (mg/1000 cycles)

Type 316L			NITRONIC 60			NITRONIC 50		
HRB 76	vs. Type 304L	11.75	HRB 99	vs. Type 304L	9.00	HRB 92	vs. Type 304L	5.04
HRC 24	vs. Type 304L	11.18	HRC 28	vs. Type 304L	9.24	HRC 29	vs. Type 304L	5.81
HRC 29	vs. Type 304L	10.61	HRC 38	vs. Type 304L	10.08	HRB 92	vs. 17-4 PH	4.11
HRB 76	vs. 17-4 PH	17.95	HRB 99	vs. 17-4 PH	15.69	HRC 29	vs. 17-4 PH	4.29
HRC 24	vs. 17-4 PH	16.22	HRC 28	vs. 17-4 PH	12.56	HRB 92	vs. Stellite 6B	1.87
HRC 29	vs. 17-4 PH	17.46	HRC 38	vs. 17-4 PH	13.25	HRC 29	vs. Stellite 6B	1.98
HRB 72	vs. Stellite 6B	5.77	HRB 99	vs. Stellite 6B	2.25			
HRB 76	vs. Stellite 6B	5.55	HRC 28	vs. Stellite 6B	2.94			
HRC 24	vs. Stellite 6B	5.53	HRC 38	vs. Stellite 6B	2.33			
HRC 29	vs. Stellite 6B	5.74						


Table 16  
Effect of Surface Finish on the  
Wear Resistance of Stainless Steels

Self-Mated Tests  
Weight Loss of Couple (mg/1000 cycles)


Emery Drift	Surface Finish micro inches (AA)	NITRONIC 60	17-4 PH	Type 430F*
60	70	2.9	82.0	380
120	21	3.2	81.4	411
240	13	2.7	86.7	403
0	5/6	3.1	84.2	412
3/0	4/5	3.1	83.2	390
electropolished	—	2.9	86.0	416

\*4000 cycles and triplicate tests


FIGURE 1  
Effect of Hardness on the  
Wear of Heat Treatable Steels

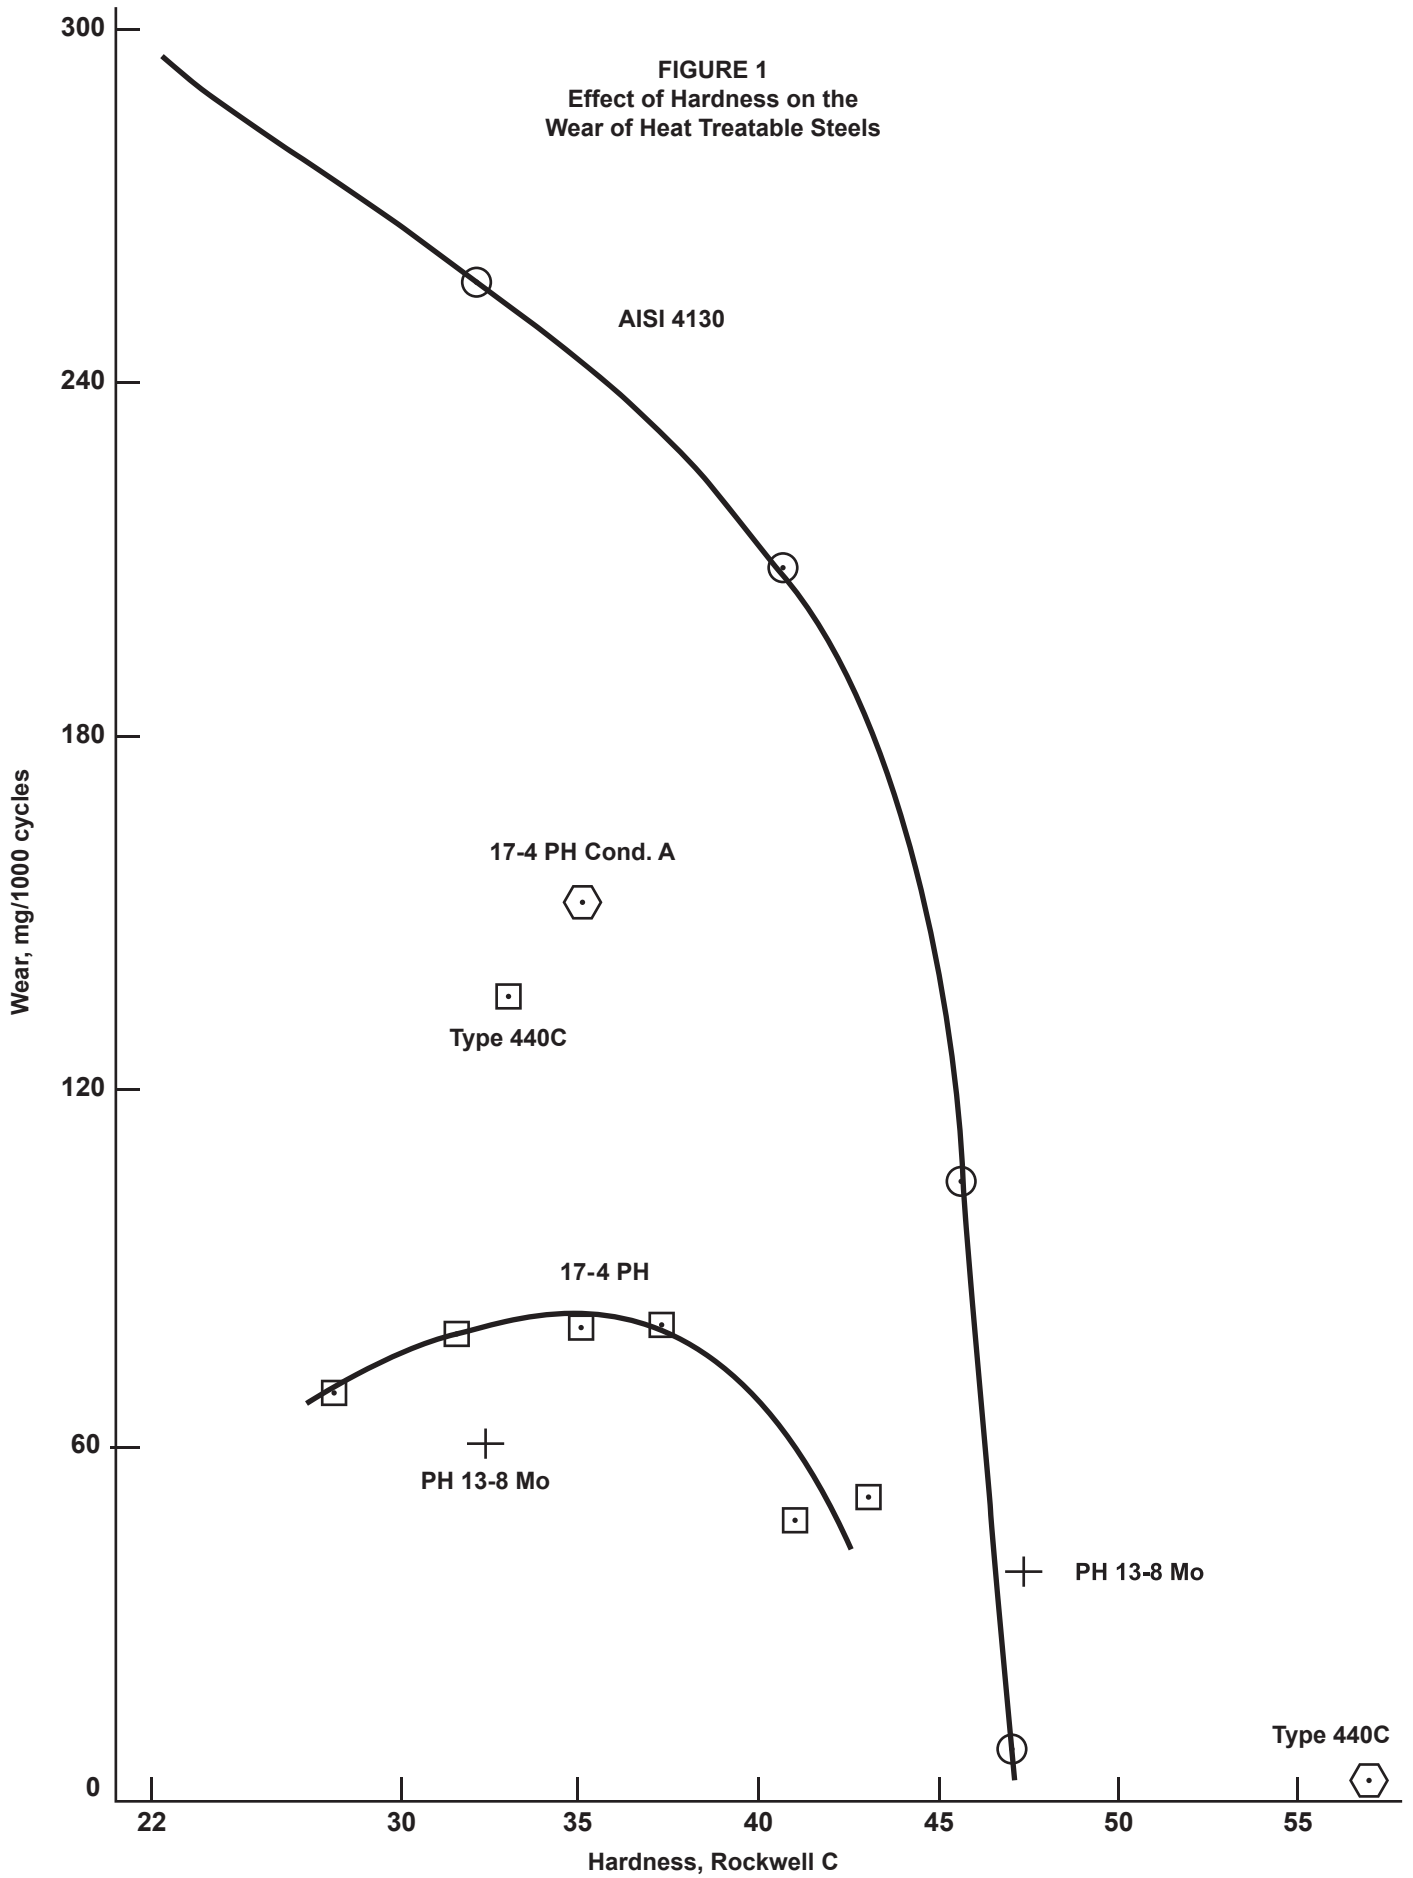


**FIGURE 2**  
Effect of Load on the Wear of NITRONIC 60 and Stellite 6B  
Taber Met-Abrader, 0.5" (12.7mm)  $\phi$  Crossed Cylinders,  
Self-Mated, 27.6 cm/sec. (415 RPM), 10,000 Cycles, Dry, in Air

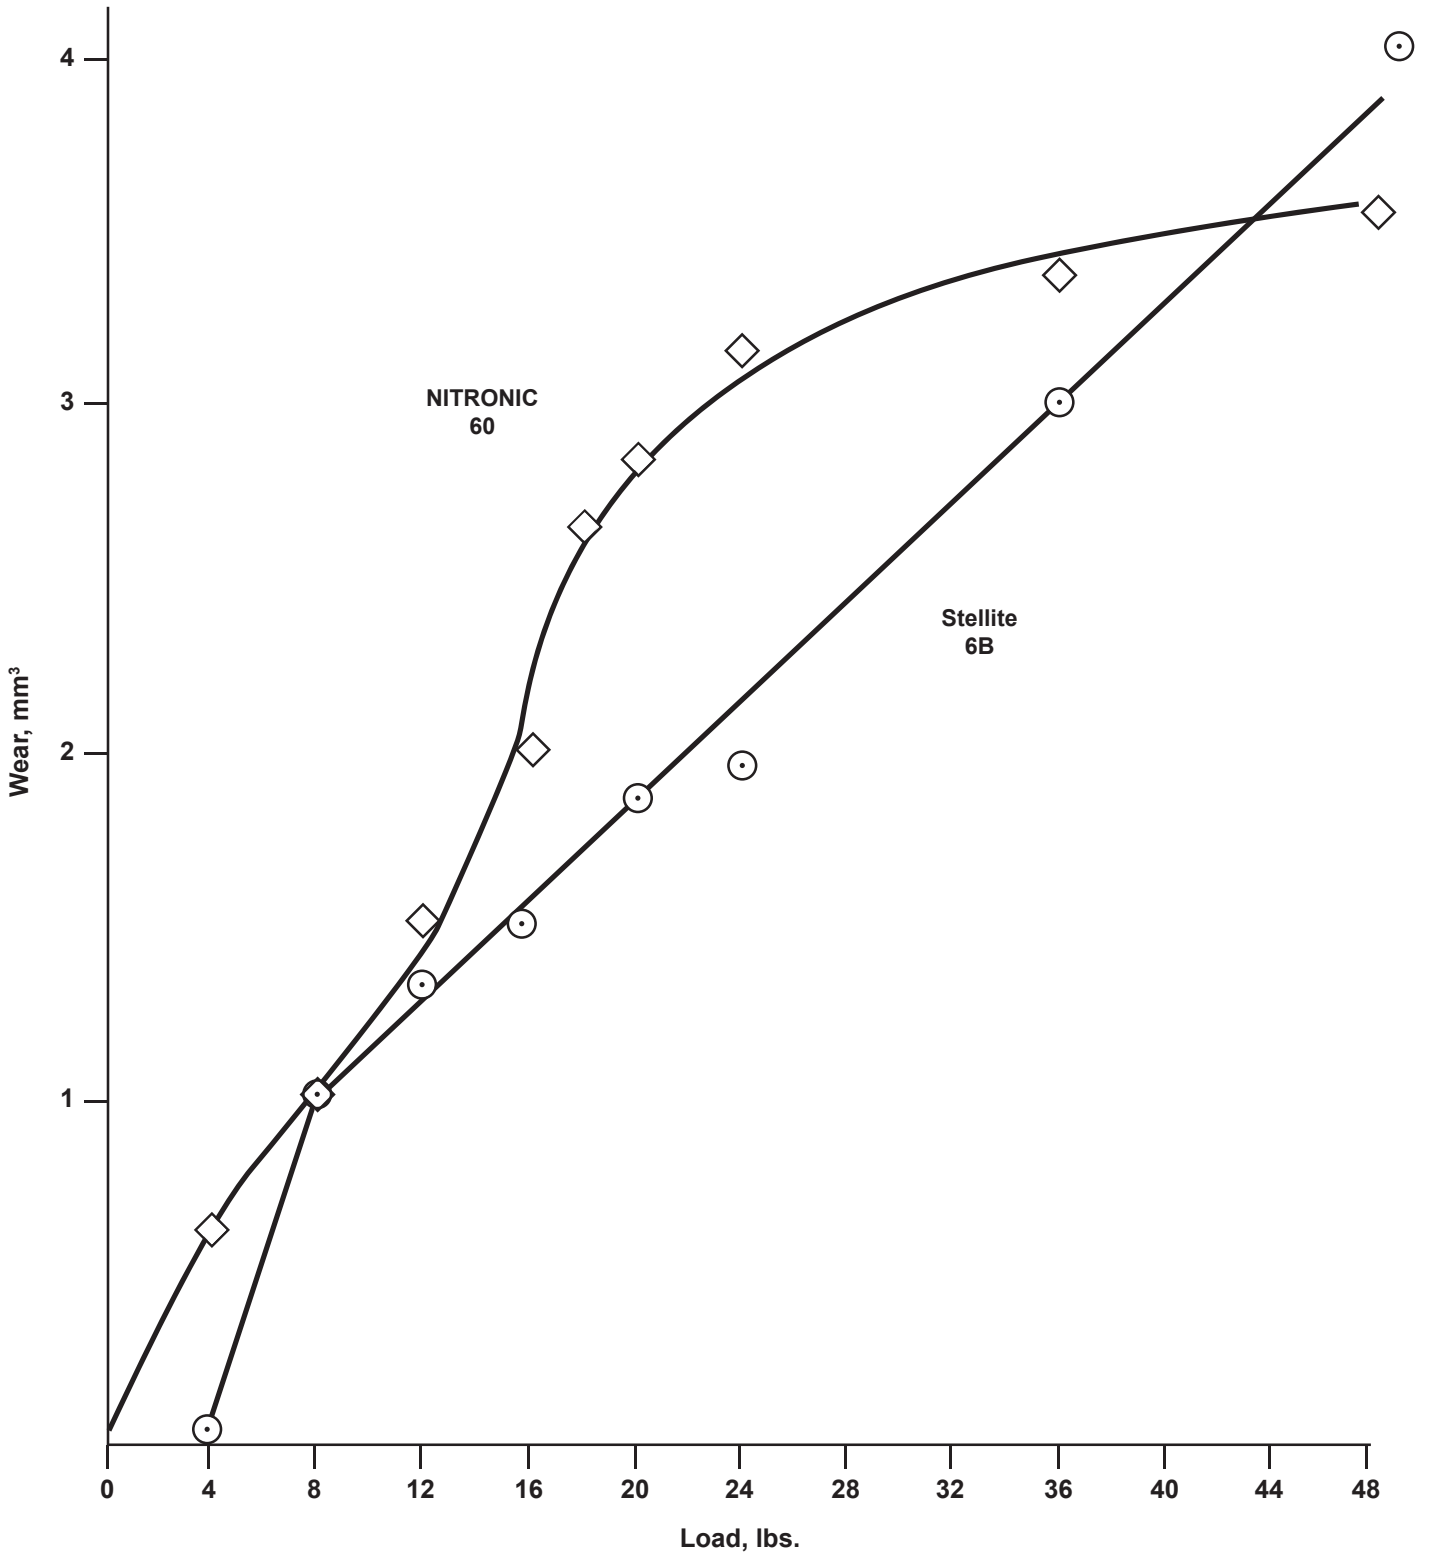

**FIGURE 3**  
**Effect of Speed on Wear**  
**16 lbs (71 N), 10,000 Cycles, Self-Mated**  
**0.5" (12.7 mm) Crossed Cylinders**  
**Corrected for Density Differences**

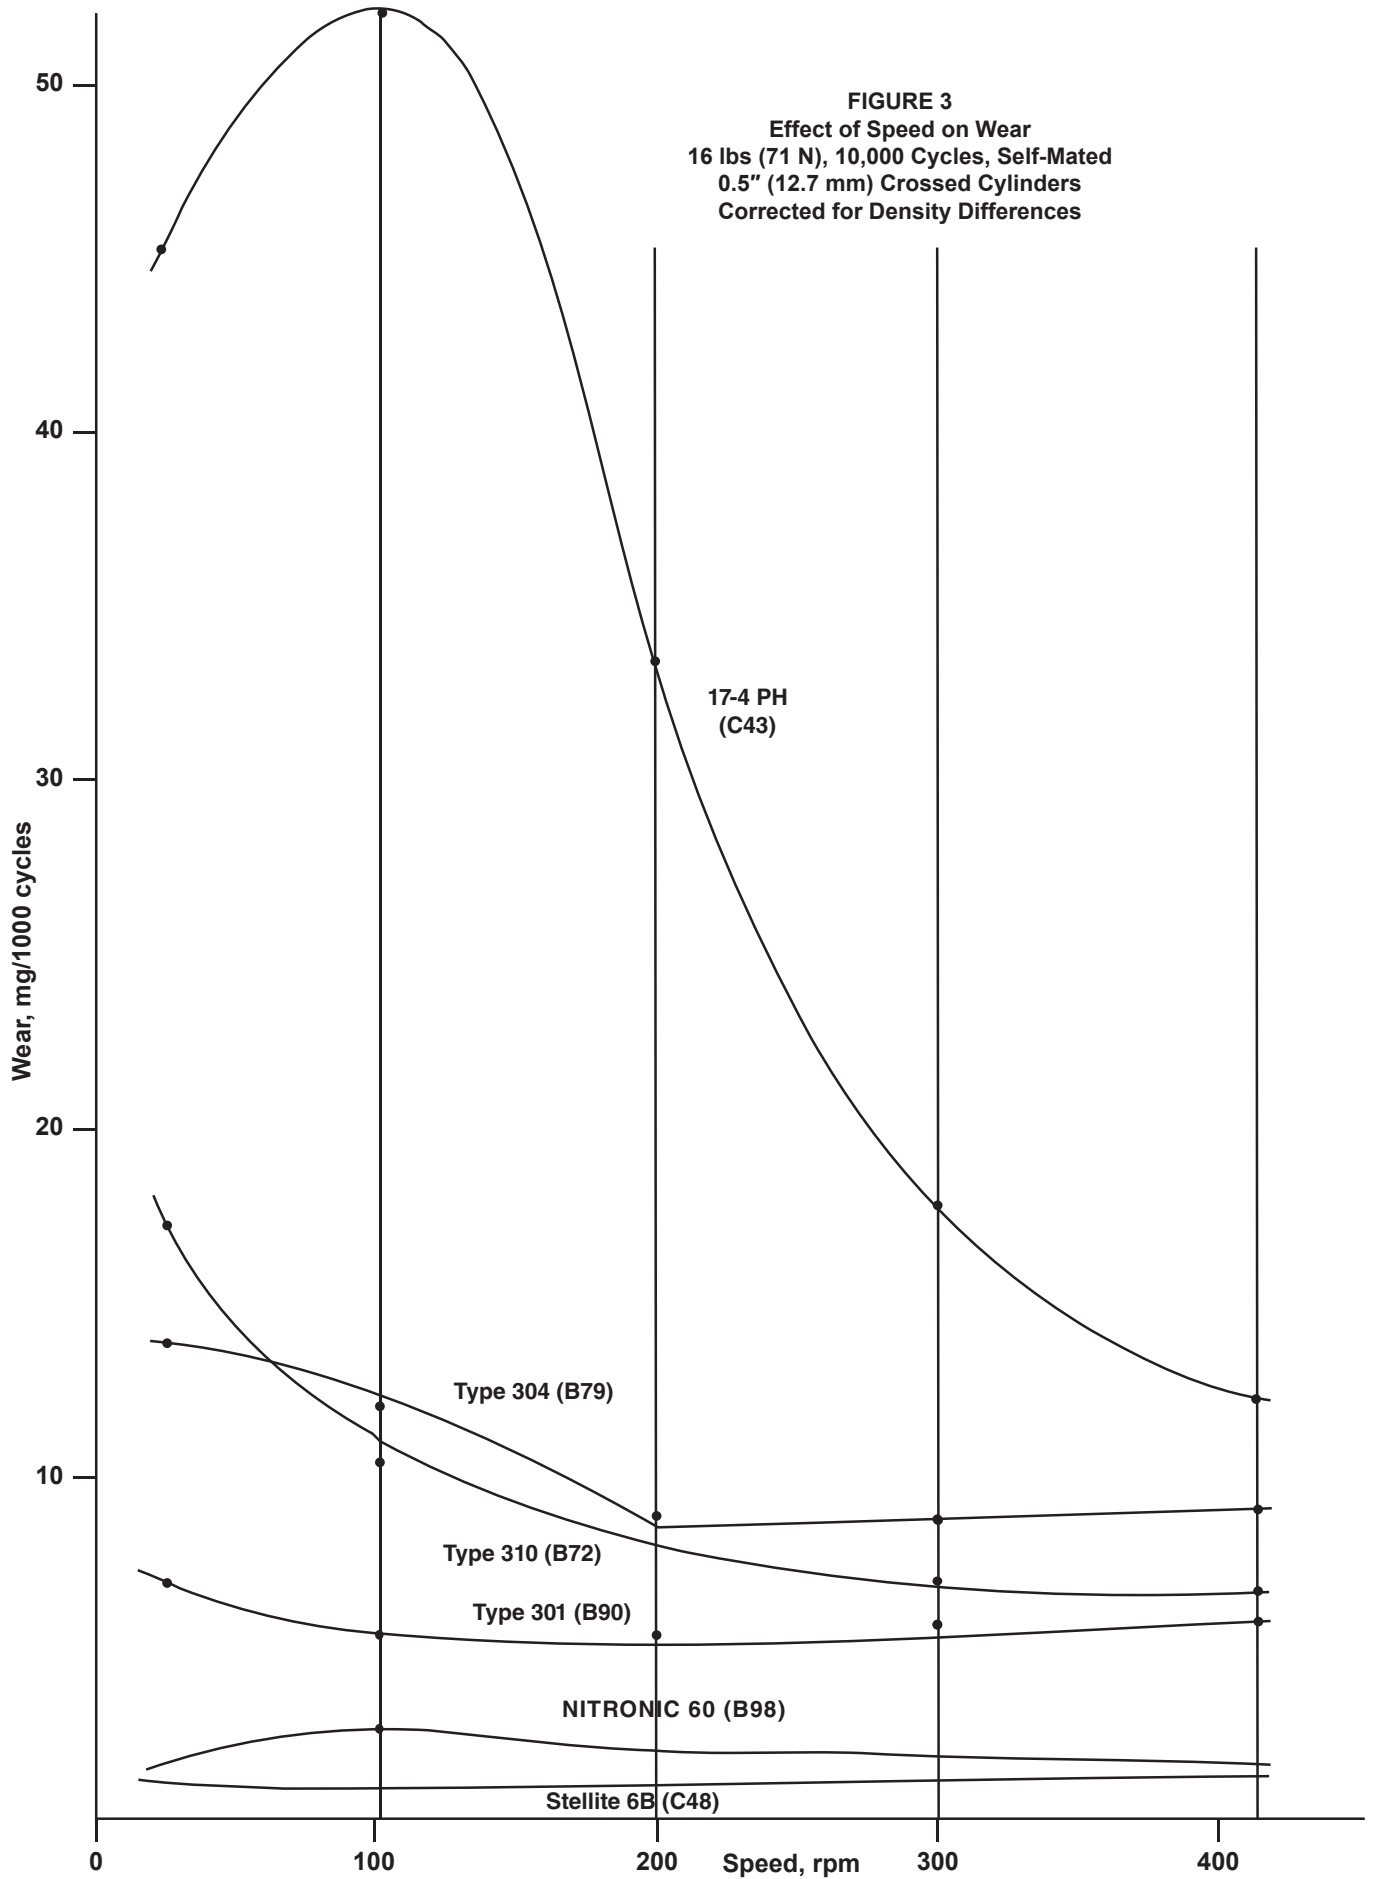


**FIGURE 4**  
**Effect of Distance on Wear Resistance of NITRONIC 60**  
**Compared to Nickel and Cobalt Alloys**

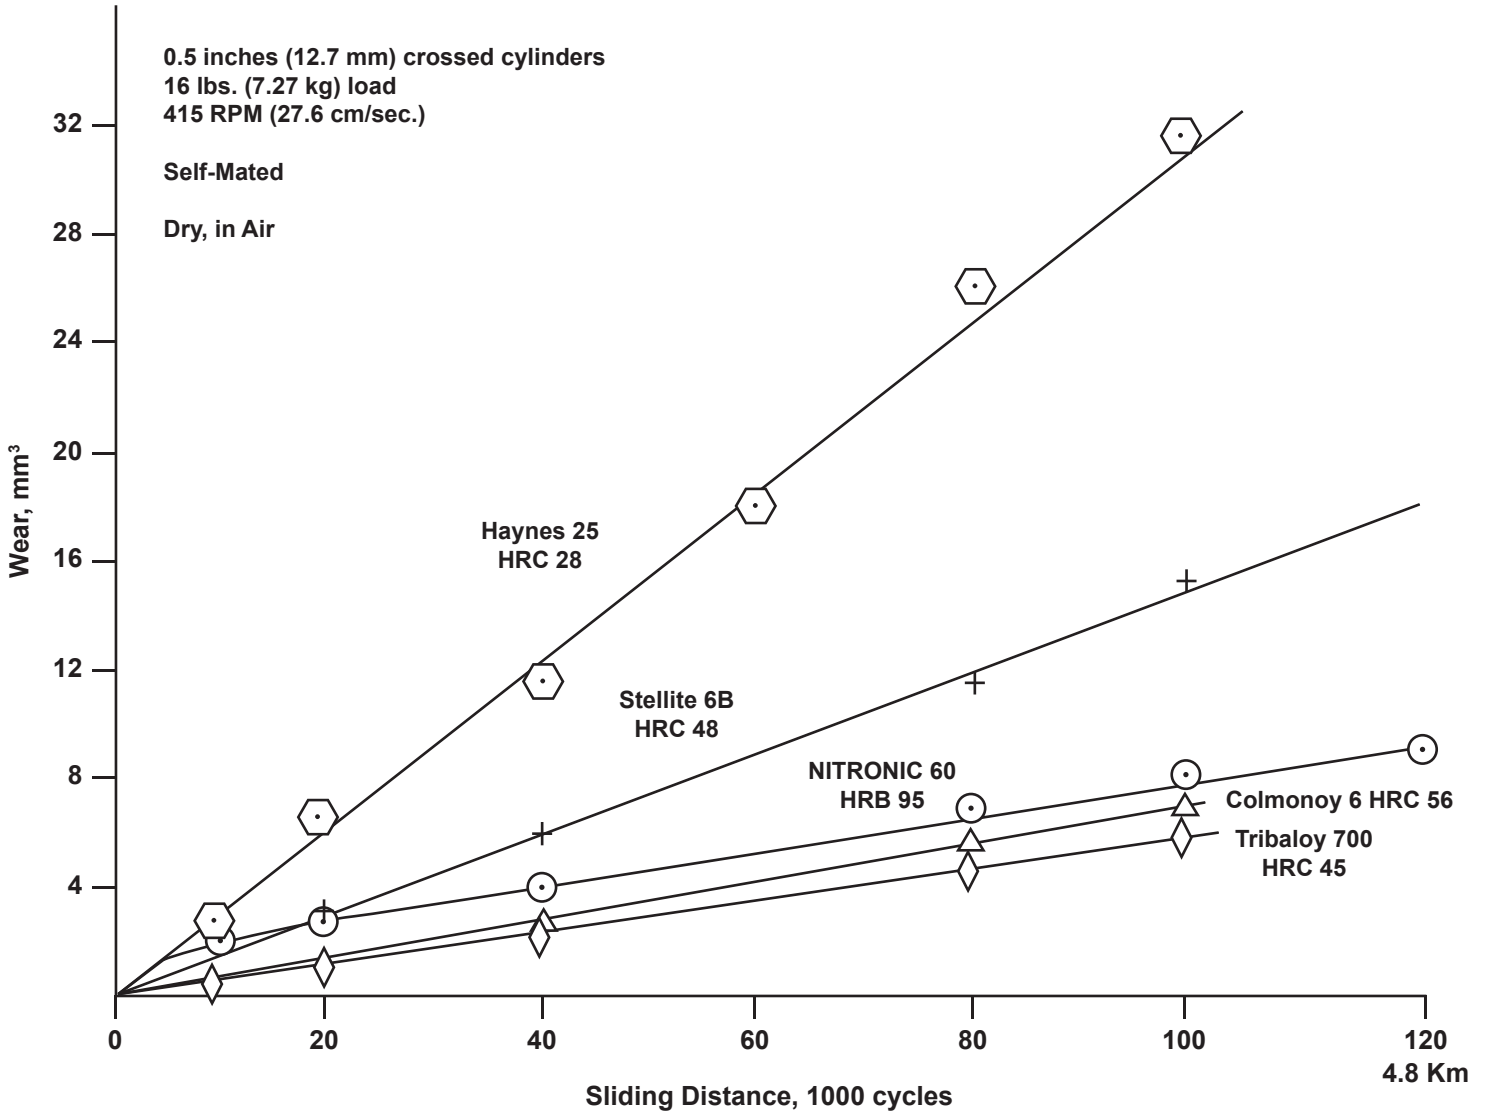

This plot of wear versus sliding distance at 415 rpm compares NITRONIC 60 stainless to nickel and cobalt alloys. NITRONIC 60 was significantly better than the two cobalt alloys. Haynes 25 and Stellite 6B, and only slightly inferior to the nickel-base alloys Colmonoy 6 and Tribaloy 700.

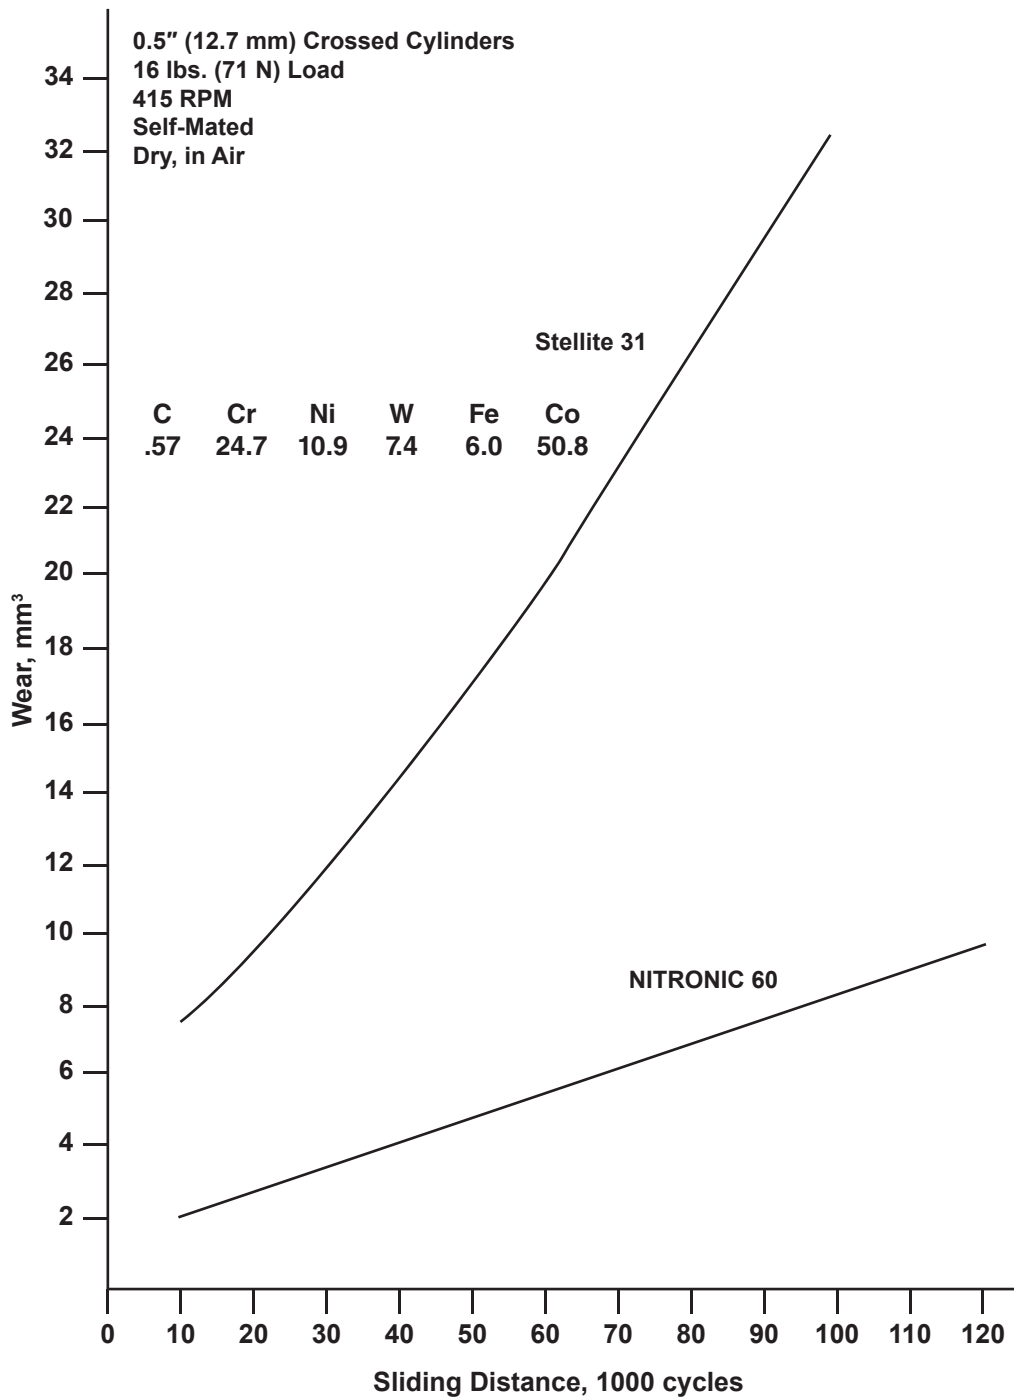**FIGURE 5**  
**Wear of NITRONIC 60 and Stellite 31**



# Elevated Temperature Wear

The elevated temperature wear resistance of NITRONIC 60 is excellent despite the alloy's relatively low hardness when compared with cobalt and nickel-base wear alloys. Armco NITRONIC 60 relies on a thin, adherent oxide film and a high strain-hardening capacity to support this film to minimize wear. NITRONIC 60 also performs well in metal-to-metal wear in nominally inert atmospheres.


Table 17  
High Temperature Wear Resistance of NITRONIC 60\*

Alloy	Atmosphere	Volume Loss, mm <sup>3</sup>	Wear Index
NITRONIC 60	Helium	6.94	38.3
	Air + Steam	8.74	30.4
NITRONIC 60	Air + Steam	10.57	25.2
Stellite 6B	Air + Steam	28.00	9.5
Type 304	Air + Steam	106.0	2.5
Mild Steel	Air + Steam	266.0	1.0 (Base)

\*Test Conditions: Self-mated thrust washers, 500°F (260°C), 500 rpm, 110 lbs (489 N), 4000 cycles. Tested at the U.S. Bureau of Mines.

\*\*Preoxidized—1000°F (538°C), 3 hours in air.

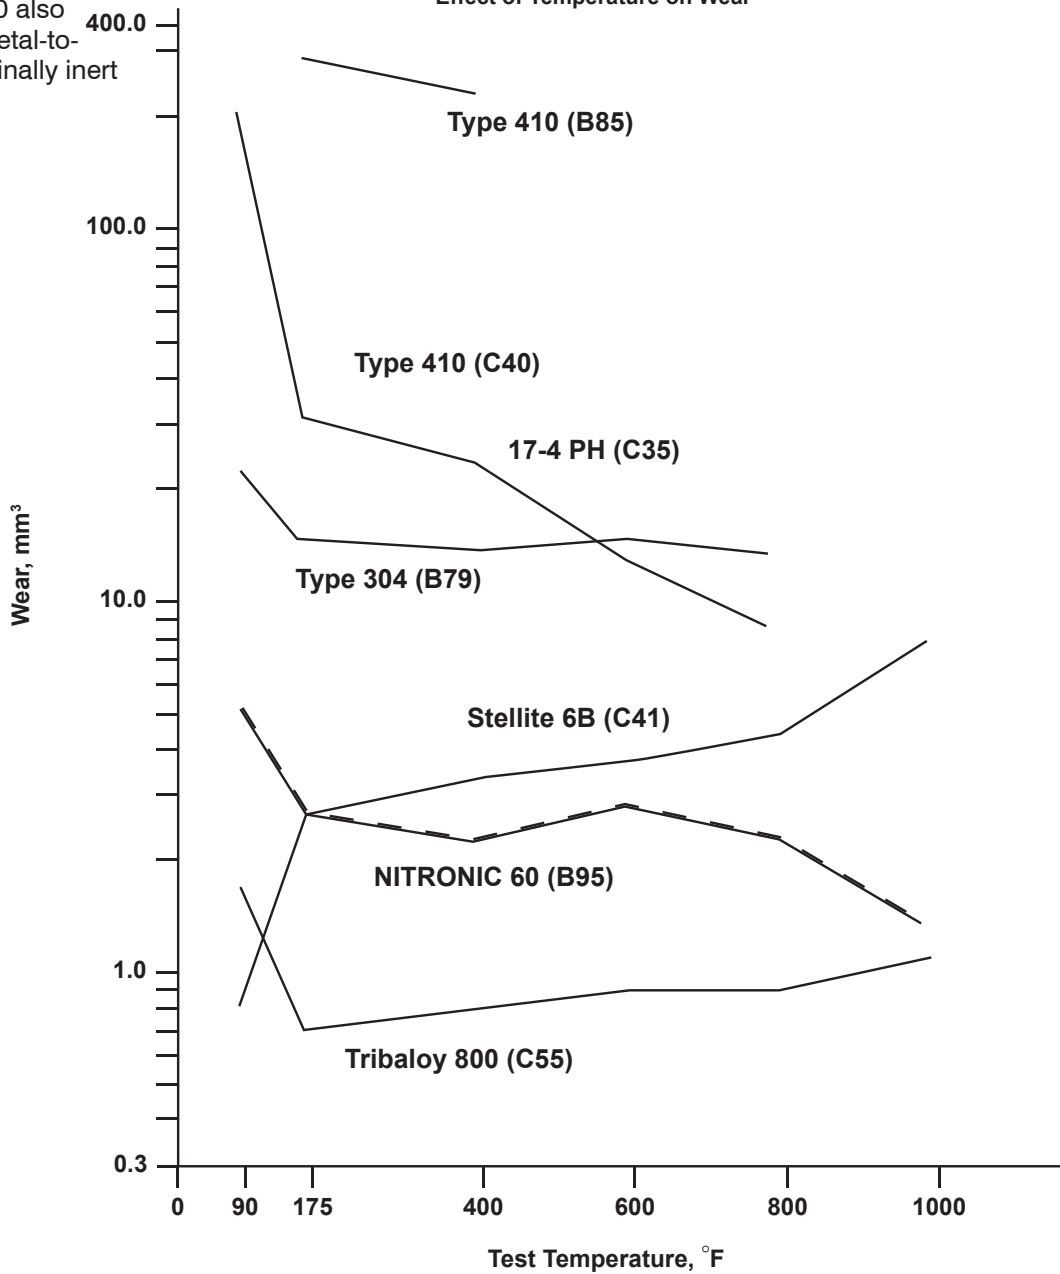FIGURE 6  
Effect of Temperature on Wear



Test conditions – 16 lbs. load, 20,000 rev., 415 RPM, self-mated, stationary specimen only heated to test temperature.

## Fretting Wear

Fretting wear is caused by high loads at very small slip amplitudes (40 μ m) such as found in vibrating components. NITRONIC 60 exhibits fretting wear at 1112° F (600° C) similar to IN 718 which has been found to be one of the most fretting-resistant alloys at this temperature.

## Cavitation Erosion

Cavitation erosion resistance of NITRONIC 60 is superior to the austenitic stainless steels as well as high strength duplex (ferritic/austenitic) stainless steels. It approaches the cobalt-base alloys which are considered among the most cavitation-resistant alloys available.

NITRONIC 60 Stainless Steel has proven highly successful for wear rings in vertical centrifugal pumps. The combination of NITRONIC 60 and NITRONIC 50 Stainless Steels has replaced cobalt wear alloys in some cases, and offers outstanding wear and corrosion protection. NITRONIC 60 Stainless Steel also has been cast up to 8550 lbs for water pump impellers where CA-6NM has proven inadequate. It is anticipated that the excellent galling resistance, cavitation erosion resistance, and good castability of NITRONIC 60 Stainless will make it an ideal choice for turbine runners, especially with integrally cast wear rings.

Table 18  
Relative Cavitation Erosion Rate

Series 1*	NITRONIC 60 1.00	Type 308L 1.89	Al Bronze 3.00	Type 304 3.67	CA-6NM 6.80	AISI 1020 15.44
Series 2*	Stellite 6B 0.67	NITRONIC 60 1.00	Duplex 255 3.33	Duplex 2205 4.33		Type 316L Type 317L 5.67
Series 3**	NITRONIC 60 1.00	Type 410 1.70	17-4 PH 1.90	Type 316 3.70	CA-6NM 6.60	
Series 4 Weld Overlays**	Stellite 6B 0.76	NITRONIC 60 1.00	Type 308L 3.38	Type 316 4.62	Al Bronze 12.4	

\*Laboratory Ultrasonic Cavitation Test Method  
20kHz, 80°F (27°C) H<sub>2</sub>O, 0.002" (0.05 mm) amplitude.

\*\*High -pressure jet impingement apparatus. All reported tests were conducted by either pump manufacturers or hydroelectric equipment end users.

Table 19  
Abrasion Resistance of Corrosion-Resistant Alloys Mated With Al<sub>2</sub>O<sub>3</sub>\*\*

Alloy	Hardness Rockwell	Alloy Wear: mm <sup>3</sup>	Al <sub>2</sub> O <sub>3</sub> Wear, mm <sup>3</sup>	Total, mm <sup>3</sup>
Speed — 105 rpm				
Tribaloy 700	C45	0.92	NIL	0.92
Colmonoy 6	C56	1.10	0.05	1.15
Stellite 6B	C48	1.63	0.18	1.81
Type 440C	C56	2.10	0.30	2.40
NITRONIC 60	B95	3.54	0.58	4.12
Type 301	B90	4.66	0.83	5.49
NITRONIC 50	C33	4.49	1.53	6.02
NITRONIC 32	B94	5.76	1.40	7.16
Type 304	B79	6.76	1.68	8.44
Type 310	B72	8.84	2.85	11.69
17-4 PH	C43	24.13	3.63	27.76
Speed — 415 rpm				
Type 440C	C56	0.73	0.15	0.88
Colmonoy 6	C56	0.84	0.10	0.94
NITRONIC 60	B95	0.98	0.28	1.26
17-4 PH	C43	1.80	0.33	2.13
Stellite 6B	C48	2.10	0.03	2.13
NITRONIC 60*	B95	2.68	0.04	2.72
Type 304	B79	5.06	1.68	6.74
Stellite 6B*	C48	8.46	NIL	8.46

\*40,000 cycles

\*\*Test Conditions: Taber Met-Abrader machine, 0.5" (12.7 mm) diameter specimen mated with 0.25" (6.4 mm) .at Al<sub>2</sub>O<sub>3</sub> in .xed position, 16 lbs. (71 N), room temperature, 10,000 cycles, dry, in air.

Table 20  
Abrasion Resistance of Corrosion-Resistant Alloys  
Mated With Tungsten Carbide\*

Alloy	Hardness Rockwell	Alloy Wear. mm <sup>3</sup> **	
		10,000 cycles @105 RPM	40,000 cycles @415 RPM
D2 Tool Steel	C61	0.09	0.35
Ni-Hard	C45	0.19	0.32
Had.eld Mn	B95	0.67	0.96
Colmonoy 6	C56	1.08	3.12
Bonde	C75	1.16	2.88
Stellite 6B	C48	1.35	4.94
Tribaloy 700	C45	1.43	3.90
Type 440C	C56	1.50	1.51
Al Bronze	B93	1.65	5.89
Haynes 25	C28	2.00	15.39
NITRONIC 60	B95	2.82	9.04
Al Bronze	B97	3.17	8.39
Type 301	B90	3.80	16.03
NITRONIC 32	B94	4.20	17.39
Type 304	B79	6.18	52.80
Type 316	B74	7.70	34.06
NITRONIC 50	B99	8.72	30.18
Type 431	C42	9.84	6.16
17-4 PH	C43	9.92	22.37
A-286	C33	13.92	36.68
Type 310	B72	15.26	39.09
Type 416	C39	59.63	285.61
X750	C36	—	51.60

\*Test Conditions: Taber Met-Abrader machine. 0.5" (12.7 mm) diameter crossed cylinders. 16 lbs (71 N), room temperature duplicates. WC in .xed position. dry. in air.

\*\*Wear to WC was almost nil in all cases and was not monitored.

## Corrosion Resistance

The general corrosion resistance of NITRONIC 60 Stainless Steel falls between that of Types 304 and 316. However, experience shows that in a wear system, a galling or seizure failure occurs .rst, followed by dimensional loss due to wear, and .nally corrosion. Galling and wear must be the .rst concerns of the design engineer. Although the general corrosion resistance of NITRONIC 60 is not quite as good as Type 316, it does offer better chloride pitting resistance, stress corrosion cracking resistance and crevice corrosion resistance than Type 316 in laboratory conditions. Corrosion tests are not normally performed on NITRONIC 60 HS.

Table 21  
Abrasion Resistance of Corrosion-Resistant Alloys  
Mated With Tungsten Carbide\*

Alloy	Hardness Rockwell	Alloy Wear. mm <sup>3</sup> — 10,000 cycles	
		@105 RPM	@415 RPM
Type 440C	C56	1.21	0.32
Colmonoy 6	C56	2.91	2.17
Stellite 6B	C41	3.46	3.45
Al Bronze	B87	7.00	5.19
NITRONIC 32	B94	7.08	6.75
NITRONIC 60	B95	7.26	5.42
DUPLEX 2205	—	19.02	6.13
NITRONIC 50	B99	21.45	9.03
Type 316	B76	22.41	15.59
Type 304	B79	25.23	13.48
Hastelloy C	B96	33.52	15.01
Type 310	B72	37.24	18.12
20 Cb-3	B99	44.82	17.51
INCONEL 600	B90	55.60	29.93
CA 6-NM	C26	66.04	118.72
17 -4 PH	C43	104.22	37.94

\*Only wear to the rotating alloy was measured.

Table 22  
Corrosion Properties\*

Media	Annealed NITRONIC 60	Annealed Type 304	Annealed Type 316	17-4 PH (H 925)
65% Boiling HNO <sub>3</sub>	0.060	0.012	0.012	0.132
1% HCl @ 35 C	0.010	0.053	—	0.024
2% H <sub>2</sub> SO <sub>4</sub> @ 80 C	0.045	0.243	0.011	0.021
5% H <sub>2</sub> SO <sub>4</sub> @ 80 C	0.521	1.300	0.060	—
5% Formic Acid 80 C	<.001	.081	<.001	0.001
33% Boiling Acetic Acid	0.011	0.151	<.001	0.006
168 F (76 C), 72 hours	No Reaction — Passed			
5% Salt Spray @95 F (35 C) (120 hours)	NITRONIC 60 exhibited resistance to general rusting comparable to Type 304			


Table 23  
Chloride Pitting Resistance\*

Media	Annealed NITRONIC 60	Annealed Type 304	Annealed Type 316	17-4 PH (H 925)
10% FeCl <sub>3</sub> @ RT (pitting test) 50 hours	0.004 gm/in <sup>3</sup> No Pits	0.065 gm/in <sup>2</sup> No Pits	0.011 gm/in <sup>2</sup> Pitted	0.154 gm/in <sup>2</sup> Pitted
10% FeCl <sub>3</sub> @ RT with artificial crevices 50 hours	0.024 gm/in <sup>2</sup> Slight	0.278 gm/in <sup>2</sup> Heavy	0.186 gm/in <sup>2</sup> Heavy	—

\*Data based on duplicate tests of three different heats, tested in acidified 10% FeCl<sub>3</sub> solution.

Table 24  
Stress Corrosion Cracking Resistance  
(Boiling 42% MgCl<sub>2</sub> — 4 notch tension specimens)

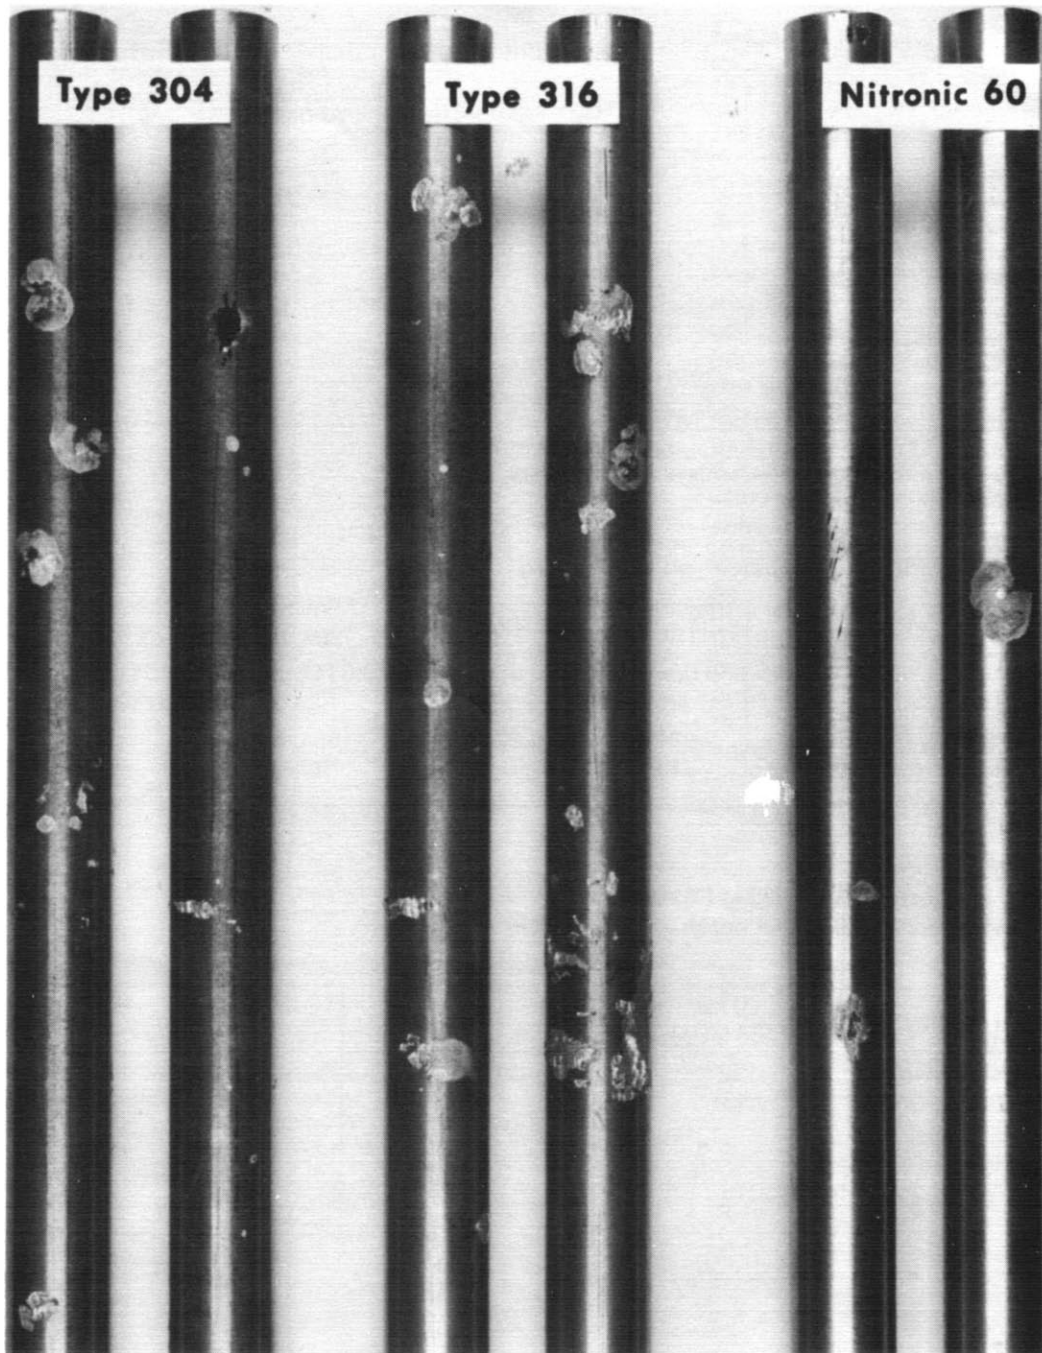Alloy	Hours to Failure at Various Stress Levels				
	20 ksi (138 MPa)	25 ksi (172 MPa)	30 ksi (207 MPa)	35 ksi (241 MPa)	40 ksi (276 MPa)
NITRONIC 60 (Number of Tests)	192 (8)	32.6 (8)	47 (2)	2.8 (1)	1.8 (6)
Type 304 (Multiple Tests)	2.3	1.9	1.5	1.2	1.0
Type 316	8	7	6	4.5	4



## Seawater Corrosion Resistance

When exposed for 6 months in quiet seawater at ambient temperature, NITRONIC 60 stainless exhibited far better crevice corrosion resistance than Type 304 and slightly better resistance than Type 316 stainless steels. These tests were run on duplicate specimens, and all grades were exposed simultaneously.

Table 25  
Sulfide Stress Cracking Resistance\*

17-4 PH (H 1150-M)			NITRONIC 60 (Annealed)		
0.2% YS ksi (MPa)	Stress Applied Expressed as a % YS	Time to Failure Hours	0.2% YS ksi (MPa)	Stress Applied Expressed as a % YS	Time to Failure Hours
108.7 (749)	90.6	8.9	55.3 (381)	110	720 (No Failure)
108.7 (749)	85.0	19.5	58.7 (405)	110	720 (NF)
108.7 (749)	81.6	21.9	52.8 (365)	100	720 (NF)
108.7 (749)	72.8	26.7	54.3 (374)	100	720 (NF)
108.7 (749)	60.7	50.1	55.3 (385)	100	720 (NF)
108.7 (749)	44.9	104.5	58.7 (405)	100	720 (NF)
110.5 (762)	34.6	214.6	58.7 (405)	85	720 (NF)
110.5 (762)	28.0	572.1	Passed NACE requirements of 720 hours stressed at 100% of 0.2% YS without failure.		
110.5 (762)	22.0	720 (No Failure)			

Table 26  
Sulfidation Resistance\*

Test Temperature F (C)	Weight Loss, mg/in <sup>2</sup>	
	NITRONIC 60	Type 309
1600 (871)	1.40	1.35
1700 (927)	2.14	3745
1800 (982)	3040	Dissolved

\*Conditions: Duplicate wire specimens placed in mixture of 90% NaSO<sub>4</sub>, 10% KCl for 1 hour at each temperature.

## Carburization Resistance

NITRONIC 60 stainless retained the best combination of strength and ductility after exposure compared to Types 316L and 309 as shown in Table 27.

Table 27  
Carburization Resistance\*

Alloy	Unexposed	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4XD	Reduction of Area %	Bend 1.5T
NITRONIC 60	Unexposed	156 (1080)	49.5 (344)	74.0	66.3	180
	Exposed	91.5 (630)	58.0 (400)	19.0	21.6	100
Type 316L	Unexposed	76.0 (524)	30.0 (207)	68.0	24.4	180
	Exposed	65.0 (448)	36.0 (248)	24.0	21.3	110
Type 309	Unexposed	99.0 (683)	41.0 (283)	54.0	64.7	180
	Exposed	85.5 (589)	45.5 (313)	14.0	11.9	75

\*Conditions: Duplicate tests, exposed at 1800 F (982 C) for 2 hours in packed 90% graphite - 10% sodium carbonate.

## Oxidation Resistance

NITRONIC 60 offers far superior oxidation resistance compared to AISI Types 304 and 316, and about the same oxidation resistance as AISI Type 309.

Table 28  
Static Oxidation Resistance\*

Test Temperature, F (C)		Weight Loss, mg/cm <sup>2</sup>			
		RA 333	Type 310	NITRONIC 60	Type 304
2100 (1149)	Before Descaling	3.1	4.6	16.5	1220
	After Descaling	12.2	15.7	23.2	1284
2200 (1204)	Before Descaling	10.1	10.1	26.1	2260
	After Descaling	16.7	20.6	35.4	2265

\*240 hours at temperature. Duplicate tests.

Table 29  
Cyclic Oxidation Resistance

Cycle	Alloy	Weight Change, mg/cm <sup>2</sup>					
		134 cycles	275 cycles	467 cycles	200 cycles	304 cycles	400 cycles
1600-1700 F (871-927 C)	RA 330	+ 3.4	+ 4.9	+ 6.4	—	—	—
25 minutes heat	Type 310	+ 4.0	+ 6.7	22.7	—	—	—
5 minutes cool	Type 309	+ 3.0	41.6	100.4	—	—	—
duplicate tests	NITRONIC 60	+ 1.5	69.2	167.6	—	—	—
		Weight Loss, mg/cm <sup>2</sup>					
1900 F (1038 C)	Type 446	—	—	—	1.47	1.72	1.97
30 minutes heat	Type 310	—	—	—	2.70	15.95	17.22
30 minutes cool	Type 309	—	—	—	22.53	26.34	33.69
	NITRONIC 60	—	—	—	42.99	60.40	74.80
	Type 316	—	—	—	93.04	135.34	178.27

## Mechanical Properties

Table 30  
Typical Room Temperature Tensile Properties\* (See Table 36 for acceptable specification values.)

Condition	Size	Hardness	UTS		0.2% YS	Elongation	Reduction
			ksi	(MPa)	ksi (MPa)	% in 4XD	of Area, %
Annealed	1" (25.4 mm) Ø	95 HRB	103	(710)	60 (414)	64	74
Annealed	1-3/4" (44.4 mm) Ø	100 HRB	101	(696)	56 (386)	62	73
Annealed	2-1/4" (57.2 mm) Ø	100 HRB	101	(696)	60 (414)	60	76
Annealed	3" (76.2 mm) Ø	97 HRB	113	(779)	65 (448)	55	67
Annealed	4-1/8" (104.8 mm) Ø	95 HRB	106	(731)	56 (386)	57	67
AMS 5848				95 min.	50 min.		1/2" over Ø
AMS 5898				100 min.	55 min.		under 1/2" Ø

\*Data based on duplicate tests  
(1) CG bar

Table 31  
Typical Bearing Properties  
ASTM E 238

Condition	Bearing Strength ksi (MPa)	Bearing Yield Strength ksi (MPa)	0.2% YS ksi (MPa)	UTS ksi (MPa)	% El in 2"	Hardness (R)
Annealed	190.5 (1313)	79.5 (548)	104.9 (723)	52.2 (360)	49.2	B90
10% Cold Rolled	212 (1462)	132.8 (916)	123.1 (849)	90.6 (625)	40.0	C26



# HPAlloys MATERIAL Capabilities

**High Strength  
NITRONIC 60**

Issued

December  
22<sup>nd</sup>, 2003

Strain Hardened Levels

High Strength NITRONIC 60

**Minimum specification levels for bar**

Strength Condition	UTS (KSI) Min.	YS (0.2%OS) (KSI) Min.	Elongation in 4xD (%) Min.	Reduction of Area (%) Min.	Hardness Max	Maximum Size
Level 1	110	90	35	55	---	4" Dia
Level 2	135	105	20	50	330 BHN	4" Dia
Level 3	160	130	15	45	---	2.5" Dia
Level 4	180	145	12	45	---	2" Dia
Level 5	200	180	10	45	---	1.5" Dia

Copyright © 2004 High Performance Alloys, Inc.

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system or transmitted, in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise, without the prior written permission of HPAlloy.

Questions & Comments:

Tel: 800-472-5569 (inside USA and Canada)

Tel: 765-675-8871 (outside USA)

Fax: 765-675-7051

Email: [service@hpalloy.com](mailto:service@hpalloy.com)

HPAlloy WEB ADDRESS:

<http://www.hpalloy.com>

FIGURE 7  
 TYPICAL ENGINEERING STRESS-STRAIN  
 CURVE OF NITRONIC 60 IN TENSION

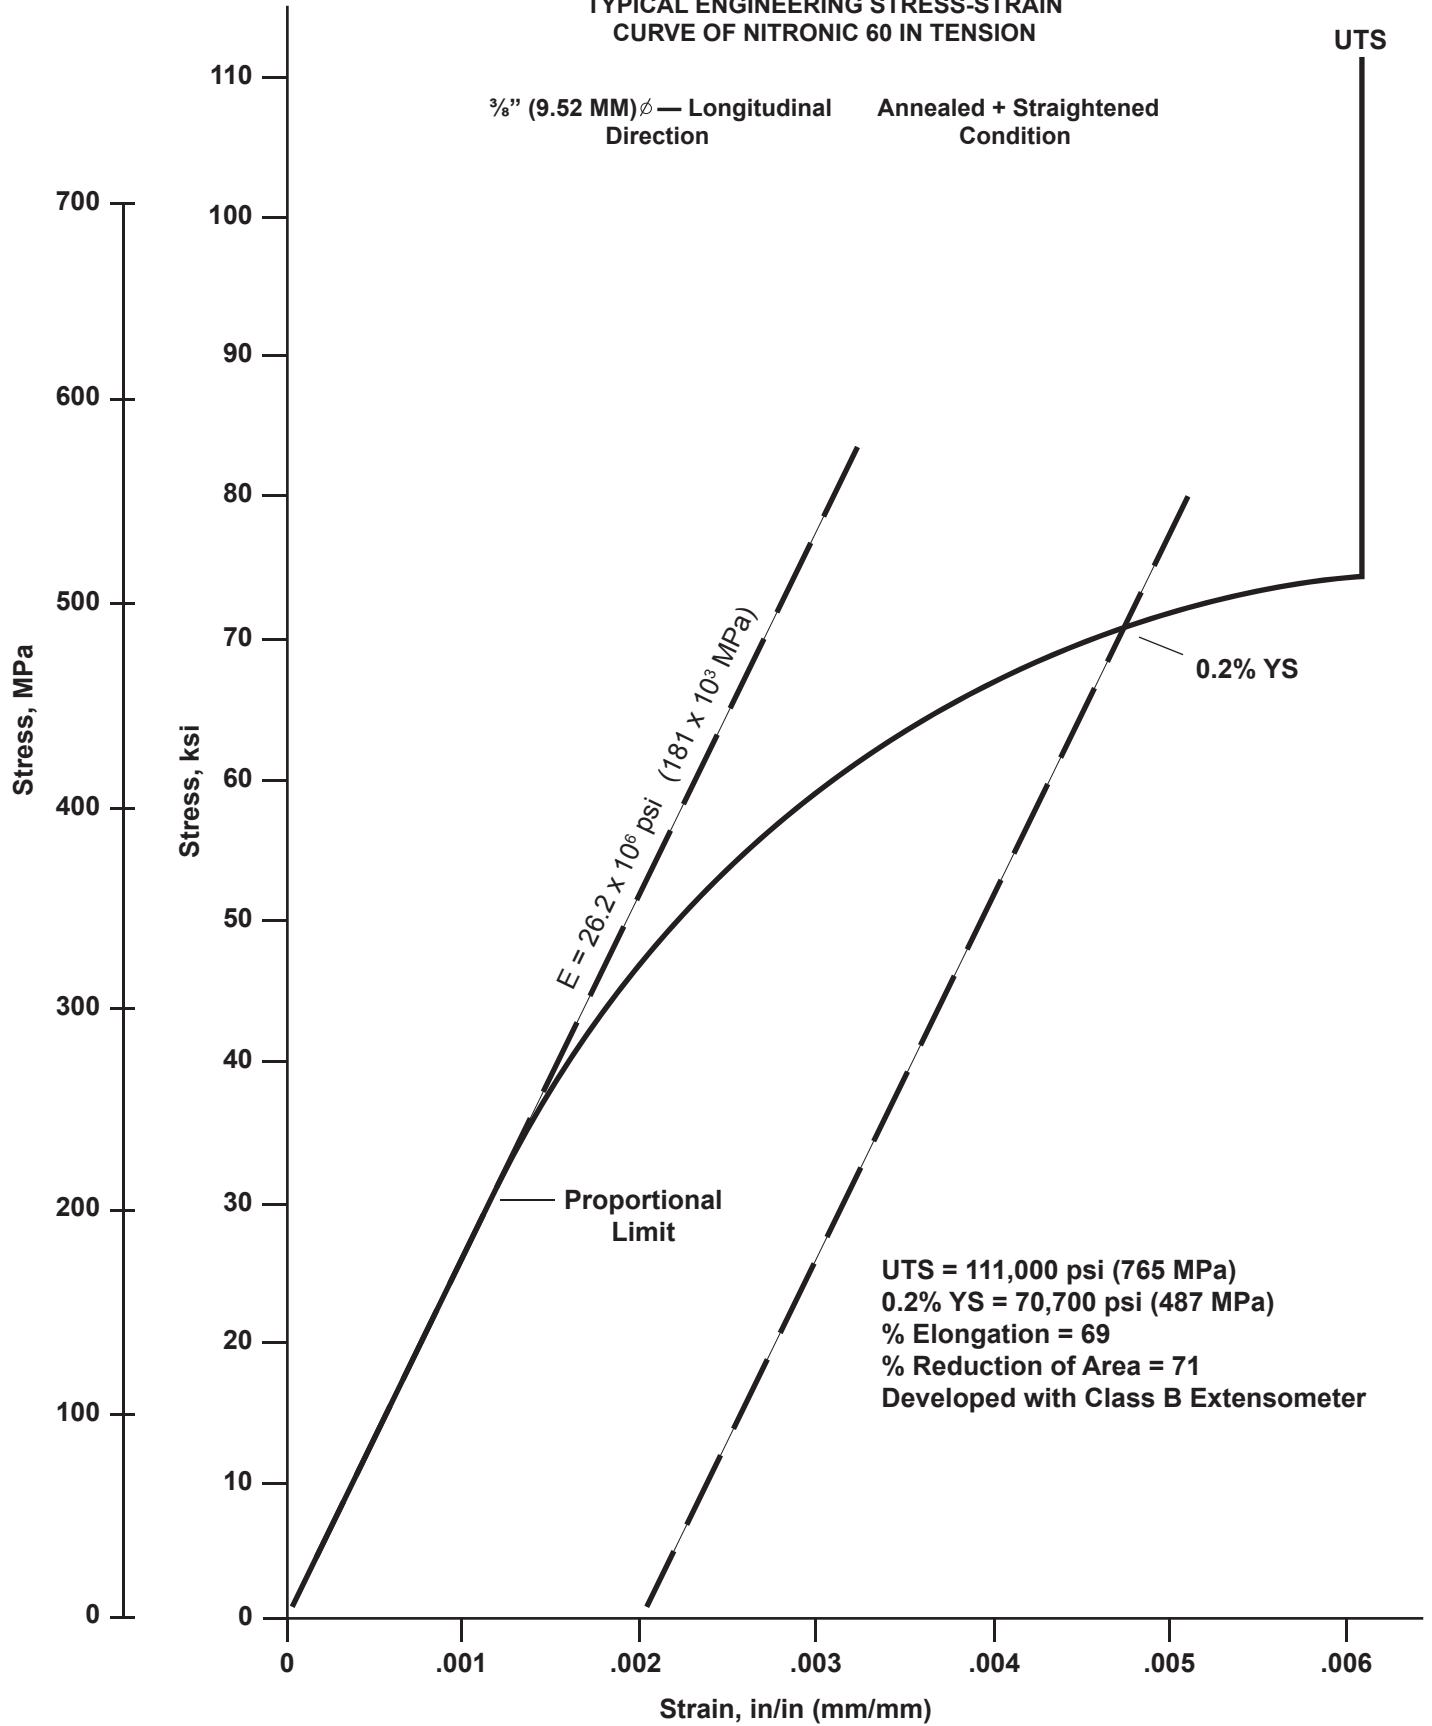


Table 32  
**Typical Room Temperature Torsion and Shear Properties\***

Condition	Size	Torsional Modulus, G ksi (MPa)	0.2% Torsional YS ksi (MPa)		Modulus of Rupture ksi (MPa)	Double Shear Strength ksi (MPa)
			$\gamma$	$\epsilon$		
Annealed	1" $\varnothing$ (25.4 mm)	95	8.83 x 10 <sup>3</sup> (61 x 10 <sup>3</sup> )	50.7 (350)	124 (855)	—
Annealed	3/8" $\varnothing$ (9.6 mm)	95	—	—	—	86 (593)

\*Data based on duplicate tests

Table 33  
**Double Shear Strength\***  
**(Cold Drawn -0.442" [11.23 mm] start size)**

% Cold Drawn	Shear Strength, ksi (MPa)
10	89 (614)
20	98 (676)
30	106 (731)
40	113 (779)
50	122 (841)
60	130 (896)

\*Data based on duplicate tests

Table 34  
**Fatigue Strength**  
**(R.R. Moore Machine)**

Condition	Size	Hardness	Fatigue Limit, ksi (MPa) 10 <sup>6</sup> Cycles
Annealed	1" (25.4 mm) $\varnothing$	95 HRB	37.5 (258)
Cold Worked 54.6%	0.70" (17.8mm) $\varnothing$	44 HRC	72.5 (500)

Table 35  
**Room Temperature Compression Strength )**

Condition	Size	0.2% Compressive YS, ksi (MPa)
Annealed	0.500" $\varnothing$ (12.7 mm)	67.6 (466)
Cold Worked 39%	0.400" $\varnothing$ (11.2 mm)	121.0 (834)

Table 36  
**Properties Acceptable for Material Specification (Bar and Wire)**

Condition	Size	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4XD	Reduction of Area, %	Hardness HRB
Annealed	1/2" $\varnothing$ + under (12.7 mm)	105 min (724)	55 min (379)	35 min	55 min	85 min
Annealed	Over 1/2" $\varnothing$ (12.7 mm)	95 min (655)	50 min (345)	35 min	55 min	85 min

Table 37

**Typical Elevated Temperature Mechanical Properties\***  
**(Annealed 3/4" and 1" [19.05 and 25.4 mm] Diameter Bar Stock)**

Test Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4XD	Reduction of Area %	Hardness Brinell
Room Temperature	106.5 (734)	56.5 (389)	61.7	71.9	200
200 (93)	98.2 (677)	44.4 (306)	63.3	72.4	187
300 (149)	89.9 (620)	37.8 (260)	64.4	73.7	—
400 (204)	84.4 (580)	32.8 (227)	64.0	73.7	168
500 (260)	82.1 (566)	32.1 (222)	61.5	73.0	—
600 (316)	80.5 (555)	29.7 (205)	59.6	73.1	155
700 (371)	79.5 (548)	29.2 (201)	59.1	72.6	—
800 (427)	78.3 (540)	29.0 (200)	56.5	72.1	148
900 (482)	77.1 (532)	28.3 (195)	53.9	71.6	—
1000 (538)	75.4 (520)	28.0 (193)	52.2	70.4	145
1100 (593)	71.6 (494)	28.7 (198)	48.7	70.0	—
1200 (649)	66.6 (459)	28.1 (194)	48.2	69.6	144
1300 (704)	59.0 (407)	27.5 (189)	41.4	50.0	—
1400 (760)	49.8** (344)	25.3 (174)	47.1	53.9	143
1500 (816)	37.0** (255)	23.8 (164)	72.8	75.0	—
1600 (871)	30.2** (208)	16.4 (113)	72.8	—	110

\*Triplicate tests of 2 heats and Single tests of 1 heat

\*\* Single tests of 1 heat

Table 38

**Elevated Temperature Tensile Properties**  
**(Cold Swaged 54% to 0.700" [17.8 mm] Ø)**

Test Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4XD	Reduction of Area %
Room Temperature	230 (1586)	216 (1489)	55	12
200 (93)	215 (1482)	205 (1413)	54	12
300 (149)	206 (1420)	199 (1372)	52	11
400 (204)	200 (1379)	194 (1338)	51	11
500 (260)	195 (1344)	191 (1317)	48	11
600 (316)	193 (1331)	188 (1296)	47	11
700 (371)	191 (1317)	176 (1213)	47	10
800 (427)	190 (1310)	184 (1269)	46	9
900 (482)	187 (1289)	177 (1220)	44	11
1000 (538)	179 (1234)	166 (1145)	47	11
1100 (593)	162 (1117)	144 (993)	52	13
1200 (649)	112 (772)	72 (496)	25	11

Table 39

**Elevated Temperature Stress Rupture Strength**  
**(Annealed Bars 5/8" to 1" [16.0 to 25.4 mm] Diameter)**

Test Temperature F (C)	Number of Heats	Stress Rupture Strength, ksi (MPa)		
		100 hr. life	1000 hr. life	10,000 hr. life
1000 (538)	3	72 (496)	52 (359)	35 (241)
1100 (593)	3	49 (338)	31 (214)	20 (138)
1200 (649)	4	29 (200)	17 (117)	10* (69)
1350 (732)	1	14 (97)	8 (55)	—
1500 (816)	1	6.7 (46)	4 (28)	—

\*Extrapolated

Table 40  
Cryogenic Tensile Properties\*

Condition	Size	Temperature, F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 4XD	Reduction of Area %
Annealed	3/8" (9.5 mm) $\emptyset$	-100 (-73)	155 (1069)	76 (524)	57	69
	3/8" (9.5 mm) $\emptyset$	-200 (-129)	170 (1172)	87 (600)	56	71
	1" (25.4 mm) $\emptyset$	-320 (-196)	213 (1469)	109 (752)	60	67
Cold Swaged	700" (178 mm) $\emptyset$	-320 (-196)	322 (2220)	272 (1875)	10	53
	54% 700" (178 mm) $\emptyset$	-200 (-129)	287 (1979)	250 (1724)	13	62

\*Duplicate tests

Table 41  
Low Temperature Mechanical Properties of  
NITRONIC 60 Stainless Steel Longitudinal Tensile Specimens\*

Test Temperature, F (C)	UTS ksi (MPa)	0.2% Offset YS ksi (MPa)	Elongation % in 1" (25.4 mm) or 4XD	Reduction of Area %	Fracture Strength ksi (MPa)	Modules psi (MPa)	N/U** Tensile Ratio	Charpy V-Notch Impact ft-lbs (J)
75 (-73)	109.3 (754)	58.1 (400)	66.4	79.0	336.1 (2317)	24.0 x 10 <sup>6</sup> (165.000)	1.44	231 (310)
0 (-129)	128.1 (883)	67.3 (464)	71.3	79.7	433.4 (2988)	23.7 x 10 <sup>6</sup> (163.000)	1.37	216 (292)
-100 (-196)	148.4 (1023)	77.9 (537)	70.5	80.9	447.1 (3083)	24.2 x 10 <sup>6</sup> (167.000)	1.45	197 (267)
-200 (-196)	167.6 (1155)	87.4 (603)	62.4	78.4	457.0 (3551)	24.2 x 10 <sup>6</sup> (167.000)	1.46	170 (231)
-320 (-129)	217.9 (1502)	101.4 (699)	59.5	65.8	594.0 (4095)	24.8 x 10 <sup>6</sup> (171.000)	1.26	138 (188)
-423 (-253)	203.8 (1405)	125.3 (864)	23.5	26.6	277.6 (1914)	24.8 x 10 <sup>6</sup> (171.000)	1.33	

\*0250' (6.35 mm) diameter, machined from a 1" (254 mm) diameter annealed and straightened bar. Four specimen average.

\*\*Average Stress Concentration Factor  $K_t = 7.0$

Data taken with permission from NASA TM X-73359. Jan. 1977.

Table 42  
Impact Properties\*\*

Condition	Size	Test Temperature, F (C)	Charpy V-Notch Impact, ft-lbs (J)
Annealed	1" $\emptyset$ (25.4 mm)	Room Temperature	240* (325)
		-100 (-73)	229 (310)
		-320 (-196)	144 (195)
Annealed	2-1/4" $\emptyset$ (54.2 mm)	Room Temperature	240* (325)
		-100 (-73)	240* (325)
		-320 (-196)	160 (217)
Cold Swaged 18% Hardness $R_C$ 29	.932" $\emptyset$ (23.7 mm)	-320 (-196)	67 (91)
Cold Swaged 40% Hardness $R_C$ 37	.795" $\emptyset$ (20.2 mm)	-320 (-196)	40 (91)
Cold Swaged 54% Hardness $R_C$ 42	.700" $\emptyset$ (17.8 mm)	-320 (-196)	26 (35)
Cold Swaged 18% Hardness $R_C$ 29	.932" $\emptyset$ (23.7 mm)	-200 (-129)	67 (91)
Cold Swaged 40% Hardness $R_C$ 37	.795" $\emptyset$ (20.2 mm)	-200 (-129)	67 (91)
Cold Swaged 54% Hardness $R_C$ 42	.700" $\emptyset$ (17.8 mm)	-200 (-129)	67 (91)

\*Did not fracture completely

\*\*Data based on duplicate tests

## High Strength (HS) Bar Properties

NITRONIC 60 Stainless Steel Bars are also available in a high-strength condition attained by special processing techniques. Because high strength is produced by mill processing, hot forging or welding operations cannot be performed on this material without loss of strength. Aqueous corrosion resistance may also be lessened to varying degrees, depending upon the environment.

Table 43  
Minimum Room Temperature Properties  
NITRONIC 60 HS Bars (Rotary Forge Only; Special Practice)

Diameter on (mm)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8mm)	Reduction of Area %	Hardness Rockwell
2.5-5.0 incl (63.5-127)	110 (758)	90 (621)	20	45	C20
Over 5-6 incl (127-152)	110 (758)	70 (483)	20	45	C20
Over 6	Not Available				

Table 44  
Typical Mechanical Properties NITRONIC 60 H Bars\*

Diameter	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8mm)	Reduction of Area %
3.5" (88.9 mm)	120 (827)	93 (641)	21	27

\* Room temperature, transverse direction. Pertains to all properties listed for HS material in this section. Values taken from tests on one heat.

Table 45  
Effect of Temperature on Tensile Properties\* NITRONIC 60 HS

Test Temperature F (C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8mm)	Reduction of Area %
-320 (-196)	211 (1455)	132 (910)	28	16
-100 (-73)	165 (1138)	108 (745)	50	58
RT	127 (876)	96 (662)	37	60
200 (93)	118 (814)	87 (600)	44	59
300 (149)	108 (745)	77 (531)	43	61
400 (204)	103 (710)	74 (510)	39	61
600 (316)	99 (683)	71(490)	41	57
800 (427)	96 (662)	69 (476)	37	63
1000 (538)	91 (627)	68 (469)	31	62
1200 (649)	74 (510)	56 (386)	42	64
1400 (760)	44 (303)	31 (214)	63	83

\*Typical values, longitudinal direction, duplicate tests.

Table 46  
Typical Sub-Zero Impact Strength  
NITRONIC 60 HS Bars (3.5" [88.9 mm] Diameter)

Test Temperature, F (C)	Charpy V-Notch Impact, ft-lbs (J)	
	Longitudinal	Transverse
RT	85 (116)	40 (54)
-50 (-46)	—	21 (29)
-100(-73)	43 (58)	18 (24)
-200 (-129)	34 (46)	—
-320 (-196)	16 (22)	6 (8)

Table 47  
**Wear and Galling Properties**  
**NITRONIC 60 HS Bars\***

Couple (Hardness, Rockwell)	Weight Loss, mg/1,000 Cycles	
	105 RPM	415 RPM
NITRONIC 60 HS (C29) -Self (C29)	2.94	1.70
NITRONIC 60 HS (C29) -17-4 PH (C43)	3.69	—
	Threshold Galling Stress, ksi (MPa)	
NITRONIC 60 HS (C29) - NITRONIC 60 (B95)	41 (283)	
NITRONIC 60 HS -17-4 PH (C43)	47+ (324)	
NITRONIC 60 HS - NITRONIC 50 (C23)	49+ (338)	
NITRONIC 60 HS -Type 316 (885)	36 (248)	
NITRONIC 60 HS -17-4 PH (C34)	37 (255)	
(H 1150 + H 1150)		

\*Metal-to-metal wear-crossed cylinders.

Table 48  
**Sulfide Stress Cracking of HS Bars\***

Applied Stress ksi (MPa)	% Yield Strength	Location	Time to Failure Hours
97 (669)	100	Surface	235
		Intermediate	160
		Central	132
73 (503)	75	Surface	302
		Intermediate	208
		Central	227
58 (400)	60	Surface	720 NF**
		Intermediate	720 NF
		Central	720 NF
49 (338)	50	Surface	720 NF
		Intermediate	720 NF
		Central	720 NF

\*NACE TM-01-77, Cortest Proof Rings, Yield Strength = 97 ksi (669 MPa)

\*\*NF -No Failure

Table 49  
**Chloride Stress Corrosion Cracking Resistance NITRONIC 60HS\***

Condition	Hardness (HR)	Result
Hot Rolled 0.1" (2.54 mm) thick strip	C36	No Failure
1950 F (1066 C) + 1300 F (704 C) -10 min. -AC** 0.06" (1.5 mm) thick strip	B92	No Failure
1950 F (1066 C) + 1450 F (788 C) -10 min -AC** 0.06" (1.5 mm) thick strip	B92	No Failure

\*U-Bends, 1-1/4" (6.96 mm) Diameter Mandrel -5% NaCl + 0.5% Acetic Acid, Boiling for 30 Days + 10% NaCl + 0.5% Acetic Acid, Boiling for 30 Days.

\*\*Simulates partially sensitized condition often found in materials used in oil exploration equipment.

## Physical Properties

Table 50  
**Physical Properties**

Density at 75 F (24 C)—7.622 gm/cm<sup>3</sup>  
 Electrical Resistivity—98.2 microhm-cm  
 Modulus of Elasticity—26.2 x 10<sup>6</sup> PSI (180,000 MPa)  
 Poisson's Ratio—0.298

Table 51  
**Mean Coefficient of Thermal Expansion**

Temperature, F (C)	in/in/°F (µm/m/°C)
75-200 (24-93)	8.8 x 10 <sup>-6</sup> (15.8)
75-400 (24-204)	9.2 x 10 <sup>-6</sup> (16.6)
75-600 (24-316)	9.6 x 10 <sup>-6</sup> (17.3)
75-800 (24-427)	9.8 x 10 <sup>-6</sup> (17.6)
75-1000 (24-538)	10.0 x 10 <sup>-6</sup> (18.0)
75-1200 (24-649)	10.3 x 10 <sup>-6</sup> (18.5)
75-1400 (24-760)	10.5 x 10 <sup>-6</sup> (18.9)
75-1600 (24-871)	10.7 x 10 <sup>-6</sup> (19.3)
75-1800 (24-982)	11.0 x 10 <sup>-6</sup> (19.8)

Table 52  
Magnetic Permeability

Condition	Magnetic Permeability
Annealed	1.003
25% Cold Drawn	1.004
50% Cold Drawn	1.007
75% Cold Drawn	1.010

Table 53  
Magnetic Permeability of HS Bar\*

Bar Location	Field Strength, Oersteds (Ampere/Metres)			
	100 (7,958)	200 (15,916)	500 (39,790)	1,000 (79,580)
Surface	1.0009	1.0040	1.0029	1.0029
Intermediate	1.0003	1.0022	1.0039	1.0029
Central	1.0013	1.0024	1.0033	1.0031

\* ASTM A342, Method 4

Table 54  
Dynamic Coefficient of Friction

Alloy	Dynamic Coefficient of Friction*					
	Test Stress Level, N/mm <sup>2</sup>					
	0.8	5.6	14.0	28.0	56.0	112.0
NITRONIC 60	.50	.35	.38	.44	.44	.44
Stellite 6B	.30	.60	.63	—	—	—
NITRONIC 32	—	—	.45	.53	.65	.58

\*Tested in water at 20°C, self-mated.

Table 55  
Dynamic Coefficient of Friction  
Ring on Block (15-45lbs [67-200 N])\*

Ring	Block	Coefficient of Friction
Type 440C	NITRONIC 60	0.4 in Argon 0.4 in Air
Type 440C	Type 304	0.4 in Air
Type 440C	Type 316	0.5 in Air

Taken from: "Friction, Wear, and Microstructure of Unlubricated Austenitic Stainless Steel," by K. L. Hsu, T. M. Ahn, and D. A. Rigney, Ohio State University, ASME Wear of Materials—1979.

## Machinability

Table 56  
Machinability\*

ANSI B 1112	Type 304	NITRONIC 60
100%	45%	23%

\*1"Ø (25.4 mm)—annealed—R<sub>B</sub> 95  
Five-hour form tool life using high-speed tools  
Data based on duplicate tests

### Suggested Machining Rates

Because of desirable metallurgical characteristics of NITRONIC 60, machinability is not easy. However, with sufficient power and rigidity, NITRONIC 60 Stainless Steel can be machined. It is suggested that coated *carbides* be considered for machining.

NITRONIC 60 machines at about 50% of the rates used for Type 304; however, when using coated carbides, higher rates may be realized. Suggestions for starting rates are:

**Single Point Turning Roughing** — 0.150" depth — 0.015"/rev feed — 175 SFM  
**Finishing** — 0.025" depth — 0.007/rev feed — 200 SFM

### Drilling

1/4" diameter hole — 0.004" /rev feed — 60 SFM  
1/2" diameter hole — 0.007"/rev feed — 60 SFM  
3/4" diameter hole — 0.010"/rev feed — 60 SFM

**Reaming**—feed same as drilling — 100 SFM These rates are suggested for carbide tools, Type C-2 for roughing, drilling, and reaming. Type C-3 for finishing.

### Side and Slot Milling

**Roughing**—0.250" depth — 0.007"/tooth feed — 125 SFM  
**Finishing** — 0.050" depth — 0.009"/tooth feed — 140 SFM

# Welding

NITRONIC 60 stainless steel is readily welded using conventional joining processes. Autogenous welds made using the Gas Tungsten-Arc process are sound, with wear characteristics approximating those of the unwelded base metal. Heavy weld deposits made using the Gas Metal-Arc process and the matching weld filler are also sound, with tensile strengths slightly above those of the unwelded base metal. Wear properties are near, but slightly below those of the base metal. Weld properties compared to unwelded base metal are shown in Table 57.

The use of NITRONIC 60 stainless steel for weld overlay on most other stainless steels and certain carbon steels develops sound deposits having properties about equal to that of an all weld deposit.

The American Welding Society has included NITRONIC 60W bare wire in AWS A5.9 as ER 218 alloy.


Table 57  
**Comparative Properties of Base Metal vs. Weld Metal**

	UTS ksi (MPa)	0.2%YS ksi (MPa)	Elongation %in2" (50.8 mm)	Red. of Area%	Hardness Rockwell	Impact Charpy V-Notch ft-lbs (J)		Galling Stress NITRONIC60 vs. NITRONIC60 ksi (MPa)
						Temperature, F (C)		
As-Welded Weld Metal G.M.A.	123 (848)	85 (586)	19	22	C25	Room	54 (73) 11 (15)	40 (276)
						-320F (-196C)		
Annealed Base Metal	103 (710)	60 (414)	64	74	B95	Room	240 + (325) 144 (195)	50+ (345)

+ Did not gall.

Following are examples of the excellent galling resistance of NITRONIC 60 in the as-deposited, weld overlay condition.

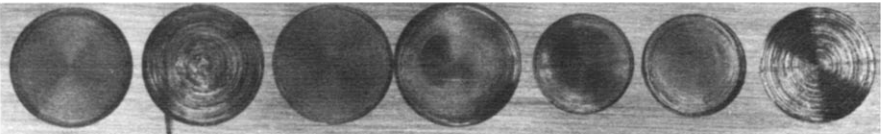
**NITRONIC 60 Galling Block**  
2 layers of NITRONIC 60 on Type 304  
GMAW Process



Mating Alloy	17-4 PH	Type 316	PH 13-8 Mo	Type 304	Type 440C	Type 410	Type 316
Contact Stress ksi (MPa)	40.8 (282) OK	40.0 (276) Galled	40.8 (282) OK	37.7 (260) OK	56.9 (392) OK	58.3 (402) OK	34.3 (236) Scored

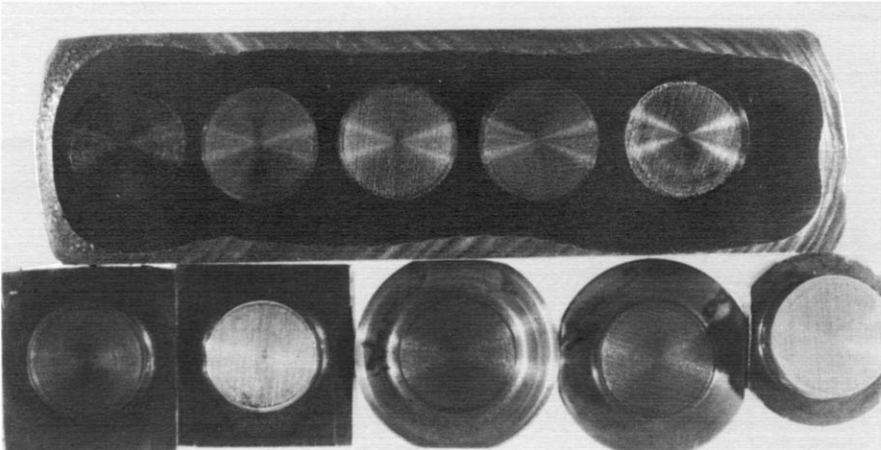**NITRONIC 60 Galling Block**  
2 layers of NITRONIC 60 on carbon steel  
Plasma Transferred Arc Process



Mating Alloy	17-4 PH	17-4 PH	Type 416	Type 416	Stellite 6B
Contact Stress ksi (MPa)	35.8 (247) OK	52.7 (365) OK	35.8 (247) OK	46.3 (319) OK	47.8 (329) OK

Table 58  
**Intergranular Corrosion Resistance of NITRONIC 60 Weld Overlay on Type 304\***

Condition	Corrosion Rate. inches/month
As-deposited	0.0016
1700 F (927 C) — 1 hr — WQ (stress relief)	0.0020
1700 F (927 C) — 1 hr — AC (stress relief)	0.0063

\*2 layers of NITRONIC 60 Stainless, gas metal-arc process. ASTM A 262 Practice B (Ferric Sulfate) Intergranular corrosion per ASTM A262 — applicable to annealed material.

Table 59  
 Typical Elevated Temperature Properties\*  
 Cast NITRONIC 60 (CF10SMnN) Annealed

Test Temperature F(C)	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area %
75 (24)	96 (662)	47 (324)	54	55
200 (93)	85 (586)	37 (255)	61	61
400 (204)	72 (496)	28 (193)	62	64
600 (316)	67 (462)	24 (165)	60	60
800 (427)	63 (434)	23 (159)	58	64
1000 (538)	61 (421)	23 (159)	57	64
1200 (649)	55 (379)	23 (159)	50	57

\* Average of 4 tests

Table 60  
 Stress Rupture Strength\*  
 Cast NITRONIC 60 (Annealed)

Test Temperature F(C)	Stress ksi (MPa)	Time to Failure hours	Elongation % in 2" (50.8 mm)	Reduction of Area %
1200 (649)	25 (172)	348	32	53
	30 (207)	108	29	48
	35 (241)	34	23	31

\* Average of tests of 11 heats  
 Data supplied by Wisconsin Centrifugal Inc.

Table 61  
 Typical Room Temperature Mechanical Properties  
 6" (152 mm) Square Cast NITRONIC 60 Stainless Steel

Condition	Location	UTS ksi (MPa)	0.2% YS ksi (MPa)	Elongation % in 2" (50.8 mm)	Reduction of Area. %	Hardness HRB	CVN Impact ft-lbs (J)
As-Cast	Surface	98 (676)	49 (338)	43	34	91	37 (50)
As-Cast	Intermediate	73 (503)	49 (338)	12	15	89	27 (37)
Annealed (Surface)	2000 F (1093 C)	101 (696)	48 (331)	62	67	91	162 (220)
Annealed (Intermediate)	2000 F (1093 C)	96 (662)	46 (317)	54	56	89	—

\* Average of tests of 11 heats  
 Data supplied by Wisconsin Centrifugal Inc.

Table 62  
 Typical Impact Strength  
 Simulated Slow Cool in Mold Study\*

Test Temperature F(C)	Charpy V-Notch Impact ft-lbs (J)
73 (22.8)	21.5 (29.2)
60 (15.6)	37.5 (50.8)

\*Cast 9" (225 mm) square x 4" (100 mm) thick section, center cooled from 2050 F to 357 F (1121 C to 191 C) in 2 hours in still air.

## WELDING GUIDELINES FOR NITRONIC 60

### General Welding

NITRONIC 60 stainless steel is readily welded using conventional joining processes. NITRONIC 60 is an austenitic stainless steel and can be handled in the weld shop like AISI 304 and 316. No preheat or post-weld heat treatments are considered necessary other than the normal stress relief used in heavy fabrication. The nature of NITRONIC 60 applications suggests that most uses would occur in the as-welded condition except where corrosion resistance is a consideration.

Fillerless fusion welds (autogenous) have been made using the gas tungsten arc process. The STA welds are free from cracking and have galling and cavitation resistance similar to the unwelded base metal. Heavy weld deposits made using the gas metal arc process are sound and exhibit higher strength than the unwelded base metal. The metal-to-metal wear resistance of the GMA welds is slightly lower than the base metal heat resistance. Detailed test results of weld metal properties are listed in Table 5 of the NITRONIC 60 product data bulletin.

Although no first-hand dissimilar weld data is available from our Armco welding laboratories, past experience suggests that NITRONIC 60 can be welded to both AISI 316 and 400 series stainless steels with Type 309 welding wire. The usual handling procedure for welding 400 series alloys would probably dictate fabricating sequence in many cases, but most specific applications require individual fabrication plans

### Repair Welding of NITRONIC 60 Castings

A simulated repair weld has been completed on a 4"x 9"x 9" section of as-cast NITRONIC 60. The welded joint was prepared by manually air-carbon-arc gouging a "V" groove and then grinding to remove carbon deposits. Developmental AMAW electrodes were used under the following conditions:

Welding current	- 130-140 Amps
Welding Voltage	- 26-28
Travel Speed	- About 8-10"/min.
Preheat Temp.	- Room Temp.
Interpass Temp.	- 300°F Max.
Post Weld Heat Treat	- None
Electrode Diameter	- 5/32"
Groove Depth	- 1 to 1.25"

After cooling to room temperature, the weldment was sectioned in several locations and dye penetrant inspected. No evidence of cracking was observed in any section.

## **WELDING GUIDELINES FOR NITRONIC 60 (CONTINUED)**

### **NITRONIC 60 Weld Overlay of Wrought and Cast Steels**

Bare wire, .062" diameter, is the most common size available for use with any filler added process that uses an inert gas shield like Gas Metal Arc, Gas Tungsten Arc, Plasma Arc, Laser, etc. The Gas Metal Arc Process may be used in any one of three modes for overlay welding; spray arc, shorting arc and pulse arc. General guidelines for the use of each are given in Table 63.

While the use of any inert gas shielded process is considered applicable for deposition, the metallurgical considerations pose a serious limitation. For example, the Gas Tungsten Arc Process with a cold wire feed, is not recommended because of the inherent high base dilution effects that make it virtually impossible to get a sound overlay - even with sub layer practices. The hot wire version of the Gas Tungsten Arc Process may work if properly controlled. Very high arc current to hot wire current ratios would have to be used to get a low base dilution (should be 25% or less). Possible parameters for a hot wire application are shown in Table 63. The intergranular corrosion resistance of NITRONIC 60 as a weld overlay on AISI 304 appears satisfactory even in the as deposited condition.

Table 63  
Welding Guidelines

	Gas Shield Metal Arc			Gas Shield Tungsten Arc
	Spray Arc	Shorting Arc	Pulse Arc	Hot Wire Feed
Gas Shield	Argon or Argon + 2% O <sub>2</sub>	Argon or Argon + 2% O <sub>2</sub> or He 90%, Ar 7.5%, CO <sub>2</sub> 2.5%	Argon or Argon + 2% O <sub>2</sub>	Argon
Gas Flow	30 CFH	30 CFH	30 CFH	30 CFH
Voltage	28032	19-22	Avg. 17-19	18
Current (Amps)	275-300	120-160	160-260	200
Weld Travel Speed	15"/min.	15"/min.	15"/min.	15"/min.
Wire Feed Speed	Adjust to give desired current	Adjust to give desired current	Adjust to give desired current	75"/min.
Hot Wire Current	—	—	—	150 Amps
Contact Tube	Should extend 1/8" out from edge of gas cup	Should extend 1/8" out from edge of gas cup	Should extend 1/8" out from edge of gas cup	—
Contact Tube to Arc Distance	Stick-out should be minimal (3/8" to 1/2")	Stick-out should be minimal (3/8" to 1/2")	Stick-out should be minimal (3/8" to 1/2")	—
Interpass Temp. (F)	Room to 350°	Room to 350°	Room to 350°	Room to 350°
Avg. Base Dilution	About 25%	About 15%	About 15%	35%
Layers Suggested	2	1 (?) 2	1 (?) 2	2

**General comment about SMAW:** Single layers with all three modes will give sound deposits. The spray arc process requires two layers due to the higher dilution. This will bring the surface closer to the original wire composition for optimum wear performance.



**HIGH PERFORMANCE  
ALLOYS, INC.**

**444 Wilson St.  
Tipton, IN 46072**

**Phone** 765-945-8230  
**Fax** 765-945-8294  
**E-mail** [sales@hpalloys.com](mailto:sales@hpalloys.com)  
**Website** [www.hpalloys.com](http://www.hpalloys.com)



**1-877-472-5569**

NITRONIC is a Registered trademark of AK Steel (Armco).